

Andrés Alessandro León Baldelli · Blaise Bourdin ·
Jean-Jacques Marigo · Corrado Maurini

Fracture and debonding of a thin film on a stiff substrate: analytical and numerical solutions of a one-dimensional variational model

Received: 15 November 2011 / Accepted: 13 April 2012 / Published online: 12 May 2012
© Springer-Verlag 2012

Abstract We study multi-fissuration and debonding phenomena of a thin film bonded to a stiff substrate using the variational approach to fracture mechanics. We consider a reduced one-dimensional membrane model where the loading is introduced through uniform inelastic (e.g., thermal) strains in the film or imposed displacements of the substrate. Fracture phenomena are accounted for by adopting a Griffith model for debonding and transverse fracture. On the basis of energy minimization arguments, we recover the key qualitative properties of the experimental evidences, like the periodicity of transverse cracks and the peripheral debonding of each regular segment. Phase diagrams relate the maximum number of transverse cracks that may be created before debonding takes place, as a function of the material properties and the sample's geometry. The theoretical results are illustrated with numerical simulations obtained through a finite element discretization and a regularized variational formulation of the Ambrosio–Tortorelli type, which is suited to further extensions in two-dimensional settings.

Keywords Variational approach · Thin films · Fracture · Delamination · Energy minimization

Communicated by Francesco dell'Isola and Samuel Forest.

A. A. León Baldelli · C. Maurini (✉)
Institut Jean Le Rond d'Alembert, UPMC Univ Paris 6, UMR 7190,
Boite courrier 161-2, 4 Place Jussieu, 75005 Paris, France
E-mail: corrado.maurini@upmc.fr

A. A. León Baldelli
E-mail: leon@dalembert.upmc.fr

A. A. León Baldelli · C. Maurini
Institut Jean Le Rond d'Alembert, CNRS, UMR 7190,
Boite courrier 161-2, 4 Place Jussieu, 75005 Paris, France

B. Bourdin
Department of Mathematics, Center for Computation and Technology,
Louisiana State University, Baton Rouge, LA 70803, USA
E-mail: bourdin@lsu.edu

J.-J. Marigo
Laboratoire de Mécanique des Solides, Ecole Polytechnique, 91128 Palaiseau, France
E-mail: marigo@lms.polytechnique.fr

1 Introduction

Thin-film systems are widely present in today's engineering solutions. Coatings, surface treatments, thermal barriers, and paintings are just to mention some. These systems are often characterized by the presence of a substrate, whose duty is to support the structural loading, and one or several layers, somehow bonded to the substrate, meant to impart a particular superficial behavior to the final assembly. The layer, or "film", as it will be called henceforth, and the substrate are often of very different material and geometric characteristics. Usually, the film is much thinner than the substrate, and its stiffness and thermal expansion coefficients may differ from those of the substrate by several orders of magnitude. Because of the assembly procedures of the final system and multi-physical loadings under working conditions (e.g., thermal loads or humidity), this mismatch may lead to significant stresses in the film and eventually lead to material failure, which can be manifested by a plethora of different and complex modes of cracking.

A detailed review of possible failure modes has been given in [1]. Isolated cracks or network of channeling fractures may develop and propagate in the overlying film, cracks originating from within the film may penetrate into the substrate, and interfacial cracks may develop in the bonding layer. Specifically, multi-fissuration and debonding are observed in a multitude of physical systems such as rocky materials and asphalts [2], microelectromechanical systems, or through drying of colloidal suspensions [3]. Considering that these systems possess very different constitutive laws and characteristic lengths spanning multiple orders of magnitude, one can argue that multi-fissuration and debonding are not specific to a particular material microstructure and should be amenable to a macroscopic description.

A common observation is that, under uniaxial loading of the specimen, a periodic network of cracks appears [4] and debonding of the film eventually takes place starting from the edges. With this starting assumption, numerous studies have been performed either with energy minimization criterions or maximum stress criterions. Multi-fissuration of thin films has been studied in [5] without accounting for the non-linear interaction with the substrate that provokes delamination. In that work, identical mechanical properties for the film and substrate have been considered. Crack spacing for a pavement layer has been studied in [2] using an elastoplastic-cohesive-frictional model for the interface. In [6], a critical stress threshold activates debonding, then an energy minimization argument is used to solve the segmentation problem. A comparison of different constitutive laws that may activate debonding are studied in [7]. In all those examples, residual friction remains where the film is debonded. The a priori knowledge of the debonded area's topology and of the crack spacing is central to the analysis also in [8] and [9].

A proper description of the complex cracking phenomena observed in thin films demands to correctly deal with complex crack geometries, crack nucleation, and evolution, which eventually may turn out to be non-smooth in space-time. These issues are known to be fundamental difficulties for the classical approach to fracture, which is based on the analysis of the propagation of a single preexisting crack along a simple and usually pre-defined path. As a result, although thin-film systems are of a great scientific and industrial interest, a general and rigorous modeling framework able to provide accurate tools for their theoretical understanding and predictive numerical simulation is still missing. A key reference for the linear fracture mechanics of thin-film systems is the work of Xia and Hutchinson [10], where the authors use a reduced two-dimensional membrane model for the film, and the substrate stiffness is accounted for as an equivalent elastic foundation. In this setting, the dimensionless parameters of the model are calibrated through finite element computations. The propagation of a single straight crack, that of an array of cracks (with the typical stop-and-go phenomenon), curved, and spiral cracks are found as particular solutions of the equation of the critical energy release rate criterion, namely $G = G_c$.

The aim of our work is to study the problem of transverse cracking and debonding of a thin film elastically bonded on a stiff substrate. To overcome the limits of classical linear fracture mechanics regarding crack nucleation and its evolution in space-time, we adopt a variational point of view. We consider a reduced model similar to that of [10], revisiting it in the framework of the variational approach to fracture mechanics as stated in [11–13]. We postulate that the cracked state of the system is given by a *unilateral global minimization principle* of a total energy functional consisting of the sum of a bulk contribution, due to the elasticity of the film and the bonding layer, and surface terms associated to the energy required to create a transverse or debonding cracks, according to Griffith model. We study the quasi-static evolution of the state of the film as a function of a single loading parameters that may be interpreted as the inelastic mismatch strain between the film and the bonding layer. We neglect rate-dependent phenomena such as inertial or viscoelastic effects, but we account for the effect of the history through irreversibility conditions on the cracks. We focus here on a $1D$ study, which includes both analytical and numerical results. Many of the assumptions that are often

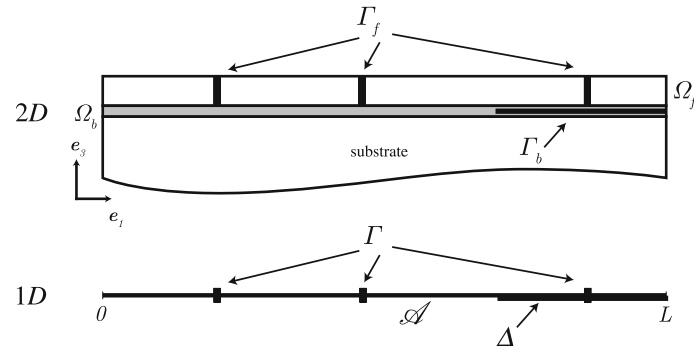


Fig. 1 2D: A cross-section of the 3D system: the film Ω_f is bonded to a stiff substrate by the means of the bonding layer Ω_b . Transverse cracks Γ_f debonding cracks Γ_b may develop in the film and in the bonding layer. 1D reduction: in the reduced uniaxial elastic bar of axis \mathcal{A} , transverse and debonding cracks are identified with Γ and Δ

postulated, namely the equidistribution of cracks, the topology of the debonded region and its activation from the boundaries, are obtained as outcomings of the variational analysis. Details about the organization of the paper and its main results are given in the following section.

The present paper shares the key ideas of the stream of works on the variational analysis of non-linear continua, to which Professor Del Piero gave several fundamental contributions [14–17]. Our work is heartily dedicated to him in occasion of his retirement.

2 Organization of the paper and main results

We start fixing some basic notation. We follow the convention of the journal to denote scalars, vectors, and tensors quantities (and analogously fields) with italic serif, bold serif, and sans serif fonts like u , \mathbf{x} , and \mathbf{e} , respectively. The derivative of a function of one variable will be indicated by a prime sign, and the Gateaux derivative of a functional $E(u, \dots)$ in the direction v will be noted $D_u E(u, \dots)(v)$. To keep the notation as light as possible, with an abuse of notation, we will sometimes denote *different* functions with the *same* symbol, provided that the number of arguments is different. Finally, we denote $\#(\cdot)$ and $\mathcal{L}(\cdot)$ the cardinal number (0-dimensional measure in \mathbb{R}^N) and the length (1-dimensional measure in \mathbb{R}^N) of a set.

We consider the system sketched in Fig. 1, where a film is bonded on a stiff substrate through a thin bonding layer. We study the appearance of transverse cracks Γ across the film's cross-section and interfacial cracks Δ along the bonding layer. Denoting by the scalar field u , the membrane displacement of the film occupying the 1D domain \mathcal{A} , we adopt a one-dimensional reduced model, which assumes that the total energy of the system is given by:

$$\mathcal{E}_t(u, \Gamma, \Delta) := \int_{\mathcal{A} \setminus \Gamma} \frac{1}{2} K (u'(x) - \bar{\varepsilon}_t)^2 dx + \int_{\mathcal{A} \setminus \Delta} \frac{1}{2} k (u - \bar{u}_t)^2 dx + G_\Gamma \#(\Gamma) + G_\Delta \mathcal{L}(\Delta), \quad (1)$$

where K is its membrane stiffness, k is an equivalent stiffness of the bonding layer, G_Γ is the energy required to create a transverse crack (transverse fracture toughness), G_Δ is the energy required to debond a unit length interval (debonding toughness), $\#(\Gamma)$ is the number of transverse cracks, and $\mathcal{L}(\Delta)$ is the total length of the debonded regions. As common in thin-film systems, the loading is represented by inelastic strains $\bar{\varepsilon}_t$ in the film (e.g., thermally induced deformations) or an imposed displacement of the substrate \bar{u}_t . We consider only the case in which $\bar{\varepsilon}_t$ is uniform and \bar{u}_t varies at most linearly throughout the domain.

The model is briefly presented in Sect. 3. After a dimensional analysis, we show that the energy (1) depends on two dimensionless parameters representing the geometric and the material properties that we choose as a scaled dimensionless film length L , a relative fracture toughness γ , and a single parameter for the loading, which we take as a scaled inelastic strain $\bar{\varepsilon}_t$. A variational formulation of the *quasi-static evolution problem* for (u, Γ, Δ) is given at the end of Sect. 3. It consists in requiring the conditions of unilateral global stability, irreversibility, and energy balance, as usually postulated in the variational theories of rate-independent processes [18].

Section 4 focuses on the *static* version of the variational problem, that is, on looking for the energy minimizers at a fixed load, without reference to any previous history or irreversibility condition. The solutions of the *quasi-static* problem are illustrated in Sect. 5. They are obtained by applying the further selection criteria of irreversibility and energy balance. We resume below the main qualitative results that are presented in the analytical part of the work:

- The solution of the problem without debonding (i.e., for infinite debonding toughness) is in the form of an equally spaced array of transverse cracks partitioning the film in n segments of length $L_i = L/n$. We give analytically the displacement field in each segment as well as the number of transverse cracks as a function of the loading (Proposition 1). In a quasi-static evolution, because of the irreversibility condition, there is a cascade of fracture phenomena in which each segment splits into two parts by a transverse fracture in its middle. Hence, the number of segments is in the form $n = 2^j$, $j \in \mathbb{N}$ (Sect. 5.1).
- In a film with finite debonding toughness divided in n regular segments by $n - 1$ transverse fractures, debonding simultaneously takes place at (one or both) the ends of each segment. The critical loading level at which this occurs is given analytically. The length of the single bonded interval of each segment is univocally determined as a function of the loading. However, solutions obtained by transferring the debonded regions from one end of a segment to any other end of any other segment are energetically equivalent (Propositions 2 and 3).
- We illustrate the possible cracking scenarios with coupled transverse fractures and debonding for specific values of the geometric and material parameters L and γ . For the static problem, we show that for low values of the load, the global minimizer of the total energy is a solution without debonding, while for high values of the load, debonding without transverse fracture is energetically preferred. Solutions with coupled transverse fractures and debonding are energy minimizers for intermediate loadings (see Proposition 4, Fig. 7). In a quasi-static evolution, there is cascade of k transverse fracture phenomena after which the film is split into $n = 2^k$ segments, followed by the debonding. After that debonded starts, no further transverse fracture appears. A numerically evaluated phase diagram (Fig. 13) gives the number k of transverse fracture phenomena before debonding, as a function of L and γ .

Section 6 focuses on the numerical solution of the quasi-static problem. The numerical implementation is based on a regularized formulation of the variational problem and a finite element discretization, which extends to the case of the thin-film energy (1) the approach of [19,20]. The quasi-static evolutions are numerically obtained by replacing the unilateral *global* stability principle, with a weaker unilateral *local* stability condition. On one hand, this is done because global minimization of non-convex functionals in high-dimensional vector spaces is numerically out of reach. On the other hand, the corresponding solutions to the evolution regularized model may be mechanically interpreted as those of a non-local damage model, where the regularization parameter can be regarded as an internal length that influences the critical loads at which fractures appear. The comparison of the solution of the quasi-static evolution problem obtained analytically and numerically allows us to validate the numerical approach and identify some shortcomings.

3 Formulation of the problem

3.1 The three-dimensional system: geometry, materials, and loadings

We consider a thin film elastically bonded to the upper surface $\omega \subset \mathbb{R}^2$ of a stiff substrate. Referring to the sketch in Fig. 1, we denote by $\Omega_f = \mathcal{A} \times (-w/2, w/2) \times (0, h_f) \subset \mathbb{R}^3$, and $\Omega_b = \mathcal{A} \times (-w/2, w/2) \times (0, -h_b) \subset \mathbb{R}^3$ the domains occupied by the film and the bonding layer in their reference configurations, $\mathcal{A} = [0, L]$ being the central axis of the film/bonding layer interface. We suppose that both the film and the bonding layer are isotropic linear elastic brittle materials, whose Young modulus, Poisson ratio, and fracture toughness are denoted by (E_f, ν_f, G_f) and (E_b, ν_b, G_b) . We distinguish two families of possible cracks: (i) debonding cracks $\Gamma_b \subseteq \Omega_b$ in the bonding layer and (ii) transverse cracks $\Gamma_f \subset \Omega_f$ inside the film. We suppose that transverse cracks are in the form $\Gamma_f \equiv (\Gamma \subset \mathcal{A}) \times (-w/2, w/2) \times [0, h_f]$, that is, that they completely cut a transversal cross-section of the film perpendicularly to the film/bonding layer interface. Similarly, we assume that the debonding cracks develop throughout the width of the strip being in the form $\Gamma_b \equiv (\Delta \subset \mathcal{A}) \times (-w/2, w/2) \times (z \in (-h_b, 0))$. In the following, we identify them by the parts of the domain \mathcal{A} that are fractured (Γ) or delaminated (Δ).

We consider two types of loadings. The first one models the effect of the substrate through an imposed displacement $\bar{\mathbf{u}}$ on the bottom surface of the bonding layer $\mathcal{A} \times (-w/2, w/2) \times \{-h_b\}$. Assuming that the

substrate is infinitely stiff compared to the film, the displacement $\bar{\mathbf{u}}$ may be obtained from the solution of the elastic problem on the substrate under structural loads when neglecting the presence of the film. Inelastic strains $\bar{\boldsymbol{\varepsilon}}$ in the film are a second type of loads. They may be defined as the deformations that the film would attain if left free from the substrate and internal compatibility constraints. The inelastic strain may rise in the system as a consequence of thermal loading, drying, or other multi-physical couplings. In the following, we assume that $\bar{\mathbf{u}}(\mathbf{x}) = \bar{u}(\mathbf{x})\mathbf{e}_1$, $\bar{\boldsymbol{\varepsilon}}(\mathbf{x}) = \bar{\varepsilon}(\mathbf{x})\mathbf{I}$, \mathbf{I} being the identity matrix.

3.2 Energy functional of the one-dimensional model

We represent the system in Fig. 1 as an elastic bar on an elastic foundation. We assume that the axis of the film undergoes axial displacement only in the form $\mathbf{u}(\mathbf{x}) = u(x)\mathbf{e}_1$. Hence, to each displacement field $u : x \in \mathcal{A} \mapsto \mathbb{R}$, fracture set Γ , and debonding set Δ , we associate the following elastic energy:

$$\mathcal{P}_t(u, \Gamma, \Delta) := \int_{\mathcal{A} \setminus \Gamma} \frac{1}{2} K (u'(x) - \bar{\varepsilon}_t)^2 dx + \int_{\mathcal{A} \setminus \Delta} \frac{1}{2} k (u - \bar{u}_t)^2 dx, \quad (2)$$

where the loadings $\bar{\varepsilon}_t$ and \bar{u}_t are parameterized by a single scalar parameter t . The first term of the energy represents the elastic energy of the film, and the integral excludes regions with transverse cracks across the film. The second term accounts for the elastic energy of the bonding layer. The integral excludes the debonded regions. The constitutive constants K and k in (2) represent the stiffness of the film and the bonding layer. An estimate of their values as a function of the material and geometric parameters of the 3D model may be obtained by assuming a state of uniaxial stress in the film and that the bonding layer undergoes pure shear. In this way one obtains:

$$K = E_f h_f w, \quad k = \frac{\mu_b w}{h_b} = \frac{E_b w}{2(1 + \nu_b) h_b}, \quad (3)$$

where $\mu_b = E_b/2(1 + \nu_b)$ is the shear modulus of the bonding layer. Adopting a Griffith model for the fracture energy, we associate to the cracks the surface energy

$$\mathcal{S}(\Gamma, \Delta) := G_\Gamma \#(\Gamma) + G_\Delta \mathcal{L}(\Delta), \quad (4)$$

where $\#(\Gamma)$ is the number of transverse cracks and $\mathcal{L}(\Delta)$ is the total length of the debonded regions. The constants $G_\Gamma = G_f h_f w$ and $G_\Delta = G_b w$ are the energy required to create a single transverse crack and the debonding energy per unit of length, respectively.

The total energy is

$$\mathcal{E}_t(u, \Gamma, \Delta) := \mathcal{P}_t(u, \Gamma, \Delta) + \mathcal{S}(\Gamma, \Delta). \quad (5)$$

Without loss of generality, we may consider the case $\bar{u}_t = 0$. This may be easily seen by applying the change of the variable $u^*(x) = u(x) - \bar{u}_t(x)$ and $\bar{\varepsilon}_t^*(x) = \bar{\varepsilon}_t(x) - \bar{u}_t'(x)$. In the sequel, we focus on the homogeneous case, for which all the material constant and the loading $\bar{\varepsilon}$ are constant in space and $\bar{u} = 0$.

Remark 1 The derivation of the one-dimensional energy above as the limit of a three-dimensional energy when h_b and h_f approach 0 can be rigorously obtained—under suitable scaling hypothesis on the thicknesses and material properties—by Γ -convergence. The proof is technical by nature and beyond the scope of this paper, but will be presented in a future work.

3.3 Dimensional analysis

Introducing a length scale x_0 and a scale for the displacements u_0 , we are able to define the dimensionless variables $x^* := x/x_0$, $u^* := u/u_0$ and denoting by \mathcal{A}^* , Γ^* and Δ^* the corresponding re-scaled axis and crack sets, one finds

$$\frac{\mathcal{E}_t(u^*, \Gamma^*, \Delta^*)}{k u_0^2 x_0} = \frac{K}{2k x_0^2} \int_{\mathcal{A}^* \setminus \Gamma^*} \left(u^{*'}(x^*) - \frac{\bar{\varepsilon}_t x_0}{u_0} \right)^2 dx^* + \int_{\mathcal{A}^* \setminus \Delta^*} \frac{u^*(x)^2}{2} dx + \frac{G_\Gamma}{k x_0 u_0^2} \#(\Gamma^*) + \frac{G_\Delta}{k u_0^2} \mathcal{L}(\Delta^*).$$

By choosing the free scaling parameters x_0 and u_0 as $x_0 = \sqrt{\frac{K}{k}}$, $u_0 = \frac{\sqrt{G_\Gamma}}{\sqrt[4]{Kk}}$, one obtains

$$\mathcal{E}_t^*(u^*, \Gamma^*, \Delta^*) := \int_{\mathcal{A}^* \setminus \Gamma^*} \frac{1}{2} (u^{*'}(x^*) - \bar{\varepsilon}_t^*)^2 dx^* + \int_{\mathcal{A}^* \setminus \Delta^*} \frac{1}{2} u^{*2}(x^*) dx^* + \#(\Gamma^*) + \gamma \mathcal{L}(\Delta^*), \quad (6)$$

with

$$\bar{\varepsilon}_t^* = \bar{\varepsilon}_t \sqrt[4]{\frac{K^3}{G_\Gamma^2 k}}, \quad \gamma = \sqrt{\frac{K}{k}} \frac{G_\Delta}{G_\Gamma}, \quad (7)$$

and $\mathcal{E}_t^* := \mathcal{E}_t / G_\Gamma$. Three dimensionless parameters determine uniquely the energy function (6): the dimensionless length of the bar $L^* = \mathcal{L}(\mathcal{A}) / x_0$, the relative bonding toughness γ , and the loading intensity $\bar{\varepsilon}_t^*$. Henceforth, we will use the non-dimensional form of the energy (6), but we will drop the $*$ for the sake of conciseness.

3.4 Quasi-static evolution problem

We consider a film free at its ends. For a given transverse fracture set Γ , the set of admissible displacement fields is independent of the debonded region Δ and belongs to the space $\mathcal{C}(\Gamma) = H^1(\mathcal{A} \setminus \Gamma)$ of square integrable displacement fields with square integrable first derivatives on $\mathcal{A} \setminus \Gamma$. The displacements may be discontinuous across the transverse cracks Γ . In this context, we start giving the following definition of quasi-static evolution, which is common in the variational theory of rate-independent processes [18, 21].

Definition 1 (*quasi-static evolution*) Given a loading path $\bar{\varepsilon}_t$ for $t \in [0, t_{\max}]$, a function $t \rightarrow (u_t \in \mathcal{C}(\Gamma_t), \Gamma_t \subset \mathcal{A}, \Delta_t \subseteq \mathcal{A})$ is a quasi-static evolution (or “the solution of the quasi-static evolution problem”) if it satisfies the Continuous Evolution Law (CEL), given by the following items:

(IR) *Irreversibility of the crack evolution*: The functions (Γ_t, Δ_t) must be non-decreasing with t , more precisely:

$$\Gamma_t \supseteq \Gamma_s, \quad \Delta_t \supseteq \Delta_s, \quad \forall 0 \leq s \leq t. \quad (8)$$

(GST) *Unilateral global stability*: At every time t , the state $(u_t \in \mathcal{C}_t(\Gamma_t), \Gamma_t, \Delta_t)$ is the *global* minimizer of the total energy among all admissible states:

$$\mathcal{E}_t(u_t, \Gamma_t, \Delta_t) \leq \mathcal{E}_t(u, \Gamma, \Delta), \quad \forall u \in \mathcal{C}_t(\Gamma), \quad \forall \Gamma \supseteq \Gamma_t, \quad \forall \Delta \supseteq \Delta_t. \quad (9)$$

(EB) *Energy balance*: The function $E(t) := \mathcal{E}_t(u_t, \Gamma_t, \Delta_t)$ is absolutely continuous in t and satisfies:

$$E(t) - E(0) = - \int_0^t \int_{\mathcal{A}} \sigma_t \frac{d\bar{\varepsilon}_t}{dt} dx dt, \quad (10)$$

where $\sigma_t := K(u_t'(x) - \bar{\varepsilon}_t)$.

In the present work, we study the quasi-static rate-independent evolution under monotonically increasing loads (MIL), that is, loadings $\bar{\varepsilon}_t$ that are monotonically increasing functions of the time t . Henceforth, we consider homogeneous proportional loadings functions of the type

$$\bar{\varepsilon}_t = t. \quad (11)$$

For MIL loadings, this is without any loss of generalization, because the evolution of a rate-independent system is defined up to a monotonic reparametrization of the time [18]. In this context, it is a common abuse of language to refer to the loading parameter t as “time”.

Remark 2 The quasi-static evolution defined above accounts for the role of time and history because of the irreversibility condition (IR). However, it neglects rate-dependent phenomena, as inertial or viscous effects. We assume that the loading rates, i.e. the derivative of $\bar{\varepsilon}_t$ with respect to t , are sufficiently small so that the system is at the static equilibrium at each loading level.

4 Solution of the static problem: energy minimizers at fixed load

Before looking for the solutions of the evolution problem, we study the crack states that are energy minimizers for a given loading, without involving any notion of history or irreversibility. We refer to this problem as the *static* problem. Formally it consists, for a given loading parameter t , in finding $u_t \in \mathcal{C}(\Gamma_t)$, $\Gamma_t \in \mathcal{A}$, $\Delta_t \in \mathcal{A}$ that verify the condition below:

(GM) *Global minimality*:

$$\mathcal{E}_t(u_t, \Gamma_t, \Delta_t) \leq \mathcal{E}_t(u, \Gamma, \Delta), \quad \forall u \in \mathcal{C}_t(\Gamma), \quad \forall \Gamma \in \mathcal{A}, \forall \Delta \subseteq \mathcal{A}. \tag{12}$$

Remark 3 The condition (GM) given in Eq. (12) is stronger than the condition (GST) given in Eq. (9). In (GST), the admissible transverse cracks and debonded sets must satisfy the irreversibility conditions $\Gamma \supseteq \Gamma_t$, $\Delta \supseteq \Delta_t$.

In the sequel, we focus first on the purely elastic case (without transverse cracks or debonding), on the uncoupled cases (transverse cracks only, then debonding only), and finally on the fully coupled model.

4.1 Elastic solution

We look for the elastic solution for a sound film, that is, the displacement field that verifies (12) for $\Delta = \Gamma = \emptyset$. The solution is unique because of the convexity of the elastic energy (linear elasticity). It must belong to $\mathcal{C}(\emptyset)$ and satisfy the first-order local minimality condition:

$$D_u \mathcal{E}(u, \emptyset, \emptyset)(v) = \int_{\mathcal{A}} ((u'(x) - t) v'(x) + u(x)v(x)) dx = 0, \quad \forall v \in \mathcal{C}(\emptyset), \tag{13}$$

where $D_u \mathcal{E}(u, \cdot, \cdot)(v)$ denotes the Gateaux derivative of the functional $\mathcal{E}(u, \cdot, \cdot)$ with respect to u along the direction v . After integration by parts, and applying standard arguments of the Calculus of Variation, one obtains that (13) implies:

$$-u''(x) + u(x) = 0 \quad \forall x \in (-L/2, L/2), \quad u'(-L/2) = u'(L/2) = t, \tag{14}$$

which are the strong formulation of the equilibrium equations plus the natural boundary conditions. They may be integrated to get

$$u_t(x) = t \frac{\sinh(x)}{\cosh(L)}. \tag{15}$$

The elastic displacement field is plotted in Fig. 2. The total energy corresponding to this solution is

$$E_t(L) := \mathcal{E}(u_t, \emptyset, \emptyset) = t^2 F(L), \quad \text{with} \quad F(L) = \left(\frac{L}{2} - \tanh\left(\frac{L}{2}\right) \right). \tag{16}$$

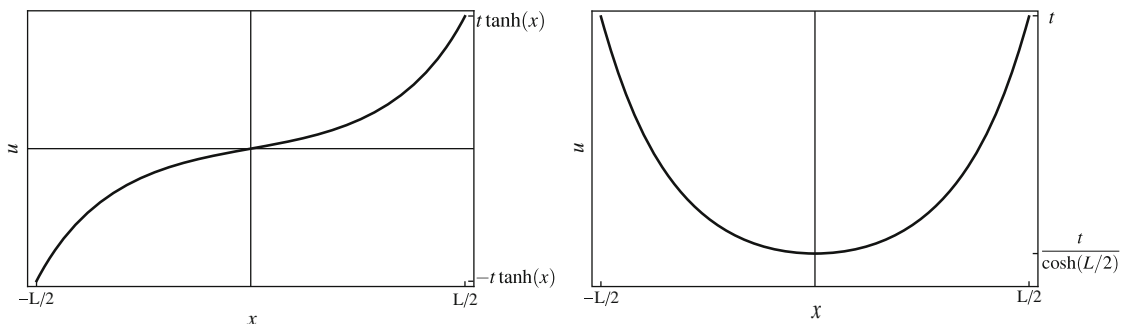


Fig. 2 Elastic displacement (*left*) and deformation (*right*) for a sound film of dimensionless length $L = 6$

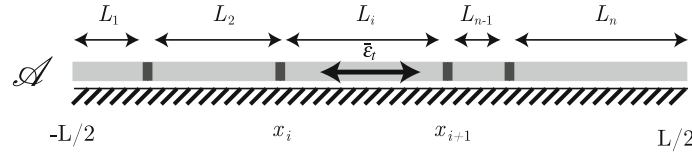


Fig. 3 A 1D film split into n pieces thus with $n - 1$ transverse cracks

4.2 Solution for a perfectly bonded film subject to transverse cracks only

We now assume that transverse cracks are free to appear everywhere, but debonding is proscribed ($\Delta = \emptyset$). The topology of the cracks in the one-dimensional setting is simple. A general state with $n - 1$ cracks is sketched in Fig. 3. The domain \mathcal{A} is split into n parts, the crack set being the set of $n - 1$ points $\Gamma^{(n)} = \{-L/2 < x_i < L/2\}_{i=1}^{n-1}$.

Each part can be seen as a sound domain of (dimensionless) length $L_i = x_i - x_{i-1}$, where $x_0 = -L/2$ and $x_n = L/2$. Hence, using the results of Sect. 4.1 and Eq. (16), the total energy of the system may be written as the following function of the number of parts n and the length of each part L_i :

$$E_t(n; L_1, \dots, L_n) = t^2 \sum_i^n F(L_i) + (n - 1). \quad (17)$$

For a fixed number of crack n , finding the optimal crack lengths L_1, \dots, L_n according to (12) consists in solving the following minimization problem

$$\min_{L_1, \dots, L_n} E_t(n; L_1, \dots, L_n), \quad \text{with} \quad \sum_{i=1}^n L_i = L, \quad L_i > 0, \quad (18)$$

which is an optimization problem for a function of n scalar variables with linear constraints. Observing that $\partial^2 E_t / \partial L_i \partial L_j = \delta_{ij} t^2 F''(L_i)$, where $\delta_{ij} = 1$ for $i = j$ and $\delta_{ij} = 0$ for $i \neq j$, and being

$$F''(L_i) = 4 \sinh(L_i/2)^4 / \cosh(L_i)^3 > 0, \quad \forall L_i > 0,$$

we conclude that the energy is a strictly convex function of L_i . Hence, the minimization problem (18) admits a unique solution, which is given by

$$L_i = \frac{L}{n}, \quad \forall i = 1, \dots, n. \quad (19)$$

This shows that the optimal crack arrangement is that of an equally distributed array of cracks throughout the film, recovering experimental evidence of periodicity of the cracks [22], without making any a priori assumption on the topology of the crack set.

The total energy of a system with $n - 1$ equally spaced transverse fractures is as follows:

$$E_t^{(n)} = t^2 \sum_i^n F(L/n) + (n - 1). \quad (20)$$

In Fig. 4, we plot $E_t^{(n)}$ as a function of t for different values of n . By (GM), the optimal number of cracks for a given load is that of the curve attaining the lowest energy. The corresponding critical loadings $t^{(n)}$ in Fig. 4 may be found analytically by looking for the intersections between $E_t^{(n)}$ and $E_t^{(n+1)}$. Hence, we conclude with the following result.

Proposition 1 *The solution of the problem (12) without debonding is that of an equally spaced array of cracks partitioning the film into n regular segments of length $L_i = L/n$. The displacement in each regular segment is in the form (15) with $L = L_i$ and the total energy of the system is given by (20). The solution with $n - 1$ cracks is optimal for*

$$t^{(n-1)} < t < t^{(n)}, \quad \text{with} \quad t^{(n)} = \frac{1}{\sqrt{(1+n) \tanh \frac{L}{2(1+n)} - n \tanh \frac{L}{2n}}}, \quad t^{(0)} := 0. \quad (21)$$

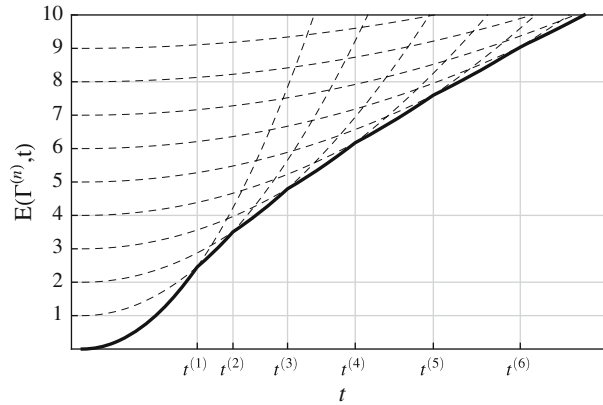


Fig. 4 Total energy for transverse fracture without debonding for different number of cracks. The cracks are equally spaced. The optimal crack number for a given loading is that of the curve attaining the lowest energy level, this last indicated by the *continuous stroke*

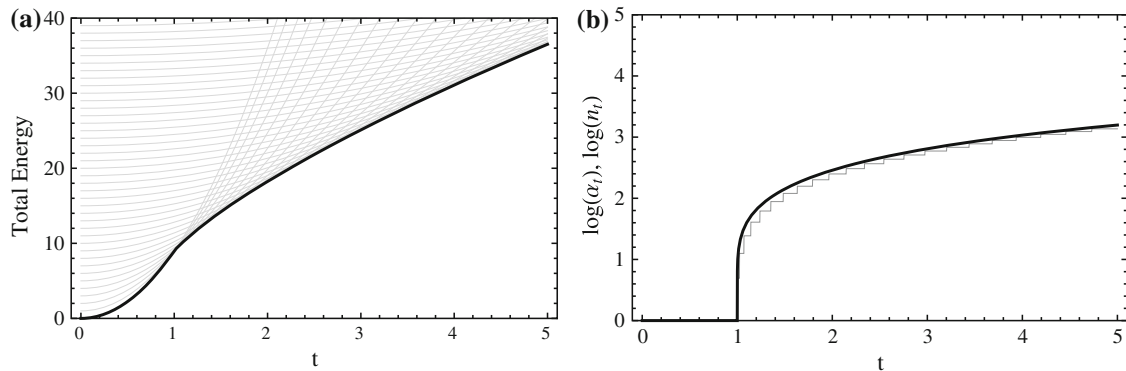


Fig. 5 Energy and fracture density curves in the “long film” regime. *Thick lines* show the results of the limit model, they are compared with the discrete family of energies (20). The limit model can macroscopically characterize high fracture density regimes with a “damage”-like parameter

Remark 4 (A limit model for long films) When the film is very long, it may be consistent to describe the system in terms of a “fracture density” rather than by the absolute number of fractures. In such setting, fracture density may be thought of as a macroscopic characterization of a damaging process. A limit model for long films is deduced from the total energy of Eq. (20) replacing the discrete variable n with the continuous density of fractures defined by $\alpha := n/L$. Minimizing the energy (20) seen as a function of α for $\alpha > 0$, we recover the envelope of the family of energies $E_t^{(n)}$, $n \in \mathbb{N}$ as Fig. 5 shows. The total energy for the limit model is displayed in Fig. 5a with a black solid line, enveloping the family of energies $\bar{E}_t^{(n)}$. In Fig. 5b we compare the discrete number n_t of cracks with the crack density α_t , in the long film regime. Both figures relate to a film of dimensionless length $L = 20$. Note that long films with transverse cracks can be regarded as an example of continua with structured deformations and modeled within the framework developed in [14].

4.3 Solution for a perfectly elastic film subject to debonding only

Introducing the characteristic function of the debonded part of the domain Δ defined as

$$\chi_\Delta(x) : x \in \mathcal{A} \mapsto \{0, 1\}, \quad \chi_\Delta(x) = \begin{cases} 1, & \text{if } x \in \Delta \\ 0, & \text{otherwise} \end{cases}$$

the total energy (6) is rewritten as follows

$$\tilde{\mathcal{E}}_t(u, \Gamma, \chi_\Delta) := \int_{\mathcal{A} \setminus \Gamma} \left(\frac{1}{2} (u'(x) - t)^2 + \frac{1}{2} u(x)^2 (1 - \chi_\Delta) + \gamma \chi_\Delta \right) dx + \#(\Gamma). \quad (22)$$

The energy density, for a fixed point $x \in \mathcal{A}$, is linear in χ_Δ . The optimality with respect to χ_Δ gives a local debonding condition depending on the value of $2\gamma/u(x)^2$, namely:

$$\chi_\Delta(x) = \begin{cases} 1, & \text{if } |u(x)| < u_c \\ 0, & \text{if } |u(x)| \geq u_c \end{cases}, \quad (23)$$

where $u_c = \sqrt{2\gamma}$ is the critical displacement threshold for debonding. The elimination of χ_Δ according to (23) allows us to rewrite the energy, and thus reformulate the problem, in terms of u and Γ alone, as follows:

$$\tilde{\mathcal{E}}_t(u, \Gamma) := \frac{1}{2} \int_{\mathcal{A} \setminus \Gamma} (u'(x) - t)^2 + f(|u(x)|) dx + \#(\Gamma), \quad (24)$$

where we introduced the non-smooth and non-convex energy density

$$f(\delta) = \begin{cases} \delta^2, & \text{if } \delta < u_c = \sqrt{2\gamma} \\ \gamma, & \text{if } \delta \geq u_c = \sqrt{2\gamma} \end{cases},$$

which accounts for both the elastic contribution of the bonding layer and the surface energy related to debonding. The energy density in (24) is non-convex with respect to u and not differentiable in u at the critical threshold u_c . According to the global minimality principle (GM), the problem of finding the solution with debonding and without transverse fractures (i.e., $\Gamma = \emptyset$) is formulated as follows:

$$\min_{u \in \mathcal{C}_t(\emptyset)} \tilde{\mathcal{E}}_t(u, \emptyset). \quad (25)$$

Unlike in the purely elastic case (Sect. 4.1), here the solution for the displacement cannot be derived using the Euler–Lagrange equations associated to the first-order local minimality condition for $\tilde{\mathcal{E}}_t(u, \emptyset)$, because of the non-differentiability of the energy density for $u = u_c$. However, the local minimizers of $\tilde{\mathcal{E}}_t(u, \emptyset)$ are characterized by the following fundamental properties, whose proofs are given in “Appendix”. Note that the present problem and the results below are very similar to those presented in [23].

Lemma 1 *If a field $u \in \mathcal{C}_t(\emptyset)$ is a local minimum of $\tilde{\mathcal{E}}_t(u, \emptyset)$, then u is a monotonic function of x .*

Lemma 2 *Let $f : \mathbb{R} \mapsto \mathbb{R}$ be a continuous function. If a field $u \in \mathcal{C}_t(\emptyset)$ is a local minimum of $\tilde{\mathcal{E}}_t(u, \emptyset)$, it satisfies the following first integral and boundary conditions:*

$$\exists C \in \mathbb{R} : \quad u'(x)^2 - t^2 - f(|u(x)|) = C, \quad \forall x \in [0, L], \quad (26a)$$

$$u'(-L/2) = u'(L/2) = t. \quad (26b)$$

The monotonicity of the solution implies that the maximal values of $|u|$ are attained at the ends of the domain. Hence, in view of the debonding condition (23), if debonding takes place, the non-debonded part of the domain is an interval, and the debonded domain is of the form:

$$\Delta = [-L/2, -L/2 + D_1] \cup [L/2 - D_2, L/2], \quad \text{with } D_1, D_2 \geq 0, \quad D := D_1 + D_2 \leq L. \quad (27)$$

Using Eq. (26), one may compute explicitly the solution with debonding, which is in the form (see Fig. 6b)

$$u(x) = \begin{cases} t(x + L/2 - D_1 + \tanh((L - D)/2)), & -L/2 \leq x \leq -L/2 + D_1 \\ t \frac{\sinh(x - x_0)}{\cosh((L - D)/2)}, & -L/2 + D_1 \leq x \leq L/2 - D_2, \\ t(x - L/2 + D_2 + \tanh((L - D)/2)), & -L/2 - D_2 \leq x \leq L/2 \end{cases}, \quad (28)$$

where $x_0 = (D_1 - D_2)/2$ is the coordinate of the center of the bonded domain. In particular, the debonded regions are stress free, and the elastic energy vanishes there. Hence, denoting by D the total debonded length and $B := L - D$ the length of the bonded interval, the total energy of the system is a function of B alone and reads as

$$\tilde{E}_t(B) := E_t(B) + \gamma(L - B) = t^2 F(B) + \gamma(L - B), \quad (29)$$

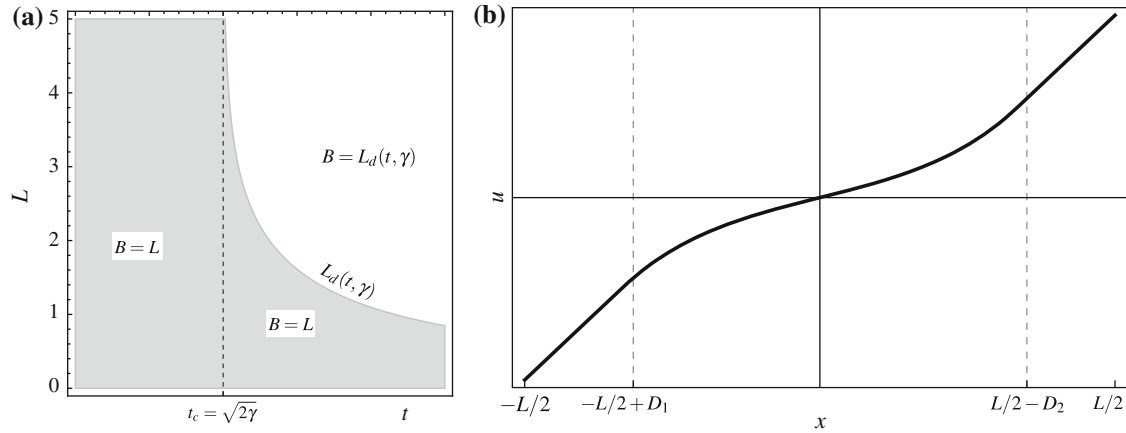


Fig. 6 Solution of (GM) for a film with debonding and without transverse fracture. **a** Phase diagram of the optimal size of the bonded domain, as function of the film length and load intensity, where $L_b(t, \gamma)$ is given in Eq. (33). **b** Displacement field for the partially bonded film, see Eq. (28)

where E_t is given by (16). For a fixed loading t , the optimal size of the debonded region solves the following problem:

$$\min_{0 \leq B \leq L} \tilde{E}_t(B), \quad (30)$$

which is the minimization of a strictly convex function of B with inequality constraints and admits a *unique* solution for the optimal bonded length $0 \leq B^* \leq L$. This solution has to satisfy the following first-order local minimality condition

$$\tilde{E}'_t(B^*)(B - B^*) \geq 0, \quad \forall 0 \leq B \leq L, \quad \text{with } \tilde{E}'_t(B) = t^2 \tanh^2(B/2)/2 - \gamma. \quad (31)$$

By the properties of convex functions, the unique minimum is attained in $B^* = 0$ if and only if $E'(0) \geq 0$, in $B^* = L$ if and only if $E'(L) \leq 0$, and in $0 < B^* < L$ such that $\tilde{E}'_t(B^*) = 0$ otherwise. The first case $B^* = 0$ is impossible because $\tilde{E}'_t(0) = -\gamma < 0$. The second case $B^* = L$ corresponds to a solution without debonding. It is obtained if and only if $t \leq \sqrt{2\gamma}$ or $L \leq 2 \operatorname{arctanh} \sqrt{2\gamma/t^2}$. For $t > \sqrt{2\gamma}$ and $L > 2 \operatorname{arctanh} \sqrt{2\gamma/t^2}$, the solution is such that $\tilde{E}'_t(B^*) = 0$, that is $B^* = 2 \operatorname{arctanh} \sqrt{2\gamma/t^2}$. This latter case corresponds to solutions with debonding.

We resume the results of the debonding of a film of length L without transverse fracture in the following Proposition:

Proposition 2 For a fixed loading t , the solution of the problem (GM) with debonding and without transverse fractures ($\Gamma = \emptyset$) is in the form (28). The displacement field u is a monotonic function of x , the bonded domain is an interval and debonding, if present, takes place at the ends of the domain. The debonded domain Δ has the form (27). The total debonded length D is uniquely determined, but the lengths D_1 and D_2 are arbitrary. The optimal length of the bonded interval is

$$B_t(L) = \begin{cases} L & \text{for } L \leq L_b(t, \gamma) \\ L_b(t, \gamma) & \text{for } L > L_b(t, \gamma) \end{cases}, \quad (32)$$

where

$$L_b(t, \gamma) := \begin{cases} \infty & \text{for } t \leq t_c = \sqrt{2\gamma} \\ 2 \operatorname{arctanh} \sqrt{2\gamma/t^2} & \text{for } t > t_c \end{cases}, \quad (33)$$

In particular, for $t \leq t_c = \sqrt{2\gamma}$, there is no debonding, independently of the film length. For $t > t_c$, the film debonds if and only if it is sufficiently long ($L > L_b(t, \gamma)$) or, equivalently, the load is sufficient high, i.e. $t > t_b(L, \gamma)$, with

$$t_b(L, \gamma) := \sqrt{2\gamma} \coth \frac{L}{2}. \quad (34)$$

The energy of the optimal solution is

$$\hat{E}_t(L) := \tilde{E}_t(B_t(L)) = \begin{cases} t^2 (L/2 - \tanh(L/2)) & \text{for } L \leq L_b(t, \gamma) \\ \gamma L + 2t^2 \left((1 - 2\gamma/t^2) \operatorname{arctanh} \sqrt{2\gamma/t^2} - \sqrt{2\gamma/t^2} \right) & \text{for } L > L_b(t, \gamma) \end{cases} \quad (35)$$

The main results are graphically illustrated in Fig. 6, which shows a phase diagram for the bonded length B as a function of (L, t) , and a snapshot of the displacement field for a partially bonded film.

4.4 Solution for a film subject to coupled transverse cracks and debonding

We now consider the case in which transverse fracture and debonding may take place at the same time in a film of length L . Suppose that the film is subdivided by $n - 1$ transverse fractures into n segments of lengths $\{L_1, \dots, L_n\}$. Given the segment length L_i , the solution for the displacement in the i -th segment is that of a film with possible debonding and without transverse fracture, which is resumed in Proposition 2. Hence, the total energy of the system may be written as follows:

$$\hat{E}_t(n; L_1, \dots, L_n) := \sum_i^n \hat{E}_t(L_i) + (n - 1),$$

where $\hat{E}_t(L_i)$, defined in Eq. (35), is the sum of the elastic and the debonding energy of the i -th segment. As in Sect. 4.2, for a fixed number of transverse cracks, the problem of finding the optimal segment lengths L_i 's may be formulated as the following constrained optimization problem:

$$\min_{L_1, \dots, L_n} \hat{E}_t(n; L_1, \dots, L_n), \quad \text{with } \sum_{i=1}^n L_i = L, \quad L_i > 0. \quad (36)$$

For $t < t_c$, the energy is strictly convex with respect to the L_i 's. As in Sect. 4.2, the solution is in the form of periodic transverse cracks without delamination, with $L_i = L/n$, and the displacement field in each segment is as in Eq. (15) and Fig. 2 (with $L = L_i$).

For $t > t_c$, the energy is not convex anymore with respect to the L_i 's. Introducing the Lagrange multiplier λ associated to the equality constraint $\sum_{i=1}^n L_i = L$, the first-order optimality conditions for (36) reads as

$$\hat{E}'_t(L_i) = \lambda \quad \text{for } i = 1 \dots n \quad \text{and} \quad \sum_{i=1}^n L_i = L. \quad (37)$$

The derivative of the energy of a single segment, $\hat{E}'_t(L_i)$, is strictly monotonic, increasing from 0 to γ , for $0 \leq L_i < L_b(t, \gamma)$ and constantly equal to γ for $L_i/n > L_b(t, \gamma)$. Hence, we may classify the solution of (37) into two types as a function of the optimal value of λ :

- (i) $\lambda < \gamma$ (*solutions without debonding*). In this case $\hat{E}'_t(L_i) = \lambda$ admits a unique solution, which is the same for each L_i . All the crack lengths must be the equal and, from $\sum_{i=1}^n L_i = L$, we find $L_i = L/n$. This is the case of periodic cracking without debonding, as in Sect. 4.2. This solution is admissible only if $L_i = L/n \leq L_b(t, \gamma)$, that is, for $t < t_b(L/n, \gamma)$, where is the $t_b(L, \gamma)$ is the critical load for debonding a film of length L given by Eq. (34).
- (ii) $\lambda = \gamma$ (*Solutions with debonding*). In this case, the problem (37) admits infinitely many solutions with $L_i \geq L_b(t)$. Even if the L_i 's are not uniquely determined, being $L_i \geq L_b(t)$, debonding is necessarily present in each segment. The length of the bonded part in each domain is $B = L_b(t, \gamma)$, and the displacement field in each segment is in the form (28) (see Proposition 2). Being $L = \sum_{i=1}^n L_i \geq n L_b(t, \gamma)$, this solution is possible only for $t > t_b(L/n, \gamma)$. Note that only the length of the bonded interval of each part is uniquely determined. The lengths L_i 's are not uniquely determined because, for each part, all the solutions obtained transferring debonded regions from one end of to the other, without changing the bonded length, are energetically equivalent.

Hence, we may conclude with the following proposition that gives the static solution with $n - 1$ transverse fractures and with free debonding as a function of t .

Proposition 3 *The solution of the problem (GM) for a film of total length L and relative fracture toughness γ with possible debonding and with $n - 1$ transverse cracks is as follows:*

- (i) For $t < t_d^{(n)} := t_b(L/n, \gamma)$ there is not debonding and the cracks are equally spaced with $L_i = L/n$.
- (ii) For $t \geq t_d^{(n)}$, there is debonding. The solution for the displacement field in each segment of the film is in the form (28) with $L = L_i$, $D_1 = D_{1,i}$ and $D_2 = D_{2,i}$. The length of the bonded interval is $L_b(t, \gamma)$ in each segment. The total debonded length is $D := \sum_{i=1}^n D_{1,i} + D_{2,i} = L - n L_b(t, \gamma)$. However, the length of the debonded parts of each segment is not uniquely determined, because all the solutions obtained by varying $D_{i,1}$, $D_{i,2}$ and keeping constant the total debonded length D have the same energy.

The total energy of the solution is

$$\hat{E}_t^{(n)} := \begin{cases} t^2 (L/2n - \tanh(L/2n)) + (n - 1) & \text{for } t \leq t_d^{(n)} \\ (\gamma L - 1) + n(1 - t^2 \varphi(\sqrt{2\gamma}/t)) & \text{for } t > t_d^{(n)}, \end{cases} \quad (38)$$

where $\varphi(x) = x + (x^2 - 1)\operatorname{arctanh}(x)$.

In order to close the problem, we must minimize $\hat{E}_t^{(n)}$ for a given load t . We are not able to provide a complete analytical solution of the latter; however, we illustrate a typical scenario for specific values of the numerical parameters with the help of the energy plot. In Fig. 7, we show the total energy versus t for different values of n , for the coupled transverse fracture-debonding problem for $\gamma = 2.2$, $L = 6$. The right figure is a zoom on the gray-shaded region. We can identify each of the curves with the corresponding value of n noticing that for a vanishing load, the energy reduces to the number of cracks $n - 1$. The dashed lines in the figure distinguished the states in which debonding has been activated. We reconstruct the optimal state of the system by comparing the energy levels in Fig. 7. For $t < t_d^{(4)}$, the optimal solution is with transverse fracture without debonding. The critical loads $t^{(n)}$, defining the range of optimality for a solution with $n - 1$ cracks, are those defined by Eq. (21). Moreover, there exists a critical load t^* beyond which the optimal solution is always that of a single delaminated segment of length $L_b(t, \gamma)$ given by Eq. (33). Indeed, for $t > t^*$, the lowest energy is always attained with $n = 1$. Such critical load is the (unique) solution of the equation: $1 - t^2 \varphi(\sqrt{2\gamma}/t) = 0$, where $\varphi(x)$ has been defined in Proposition 3. The critical time t^* is indicated in Fig. 7 with a solid vertical line. The range of loading parameter for which there is a true coupling between debonding and transverse fracture is $t^{(4)} \leq t \leq t^*$. To better illustrate the solution, we report in Fig. 8 the optimal displacement field for the following three representative loadings:

- $t = 3.00$, Fig. 8a: the minimum of the energy is attained on the energy curve relative to $n = 4$, at the point A in Fig. 7. The load is below the debonding threshold $t_d^{(4)} = 3.22$ associated to $n = 4$. The film is in the periodic multifissuration regime, with three transverse fractures.
- $t = 3.30$, Fig. 8b: the minimum energy is attained at the point B of Fig. 7 on the energy branch for which debonding is active (dashed line). The energy curve is associated to $n = 4$, and the value of the bonded domain size, for each of the four segments into which the film is split, is $B_t = 1.16$.
- $t = 4.51$, Fig. 8c: the global energy minimizer is the state without transverse fractures denoted by the point C in Fig. 7. The film is bonded on a domain of size $B_t = 1.08$.

This result may be extended to generic values of L and γ as follows.

Proposition 4 *For a film of length L and relative debonding toughness γ , let \bar{n} be the smallest (positive integer) value of n for which $t_d^{(n)} < t^{(n+1)}$ and let t^* be the (unique) root of $1 - t^2 \varphi(\sqrt{2\gamma}/t) = 0$. Then the solution of the static problem (GM) with free transverse fracture and debonding is in the following form:*

- For $t < t_d^{(\bar{n})}$, it is with transverse fractures only, with $n - 1$ equally spaced cracks in each loading interval $t^{(n-1)} < t < t^{(n)}$ with $n \leq \bar{n}$, as in Proposition 1.
- For $t > t^*$ it is with debonding only, as in Proposition 2.

The number \bar{n} is the minimum number of parts in which a film is split by transverse fractures when there is debonding. The dependence of \bar{n} and t^* on the two dimensionless parameters L and γ is illustrated numerically in Fig. 9. The critical load t^* is independent of L .

For loadings in the interval $t_d^{(\bar{n})} < t < t^*$, there is a non-trivial coupling between transverse fracture and debonding, and we cannot derive a general and simple result of what can happen for generic values of γ and L .

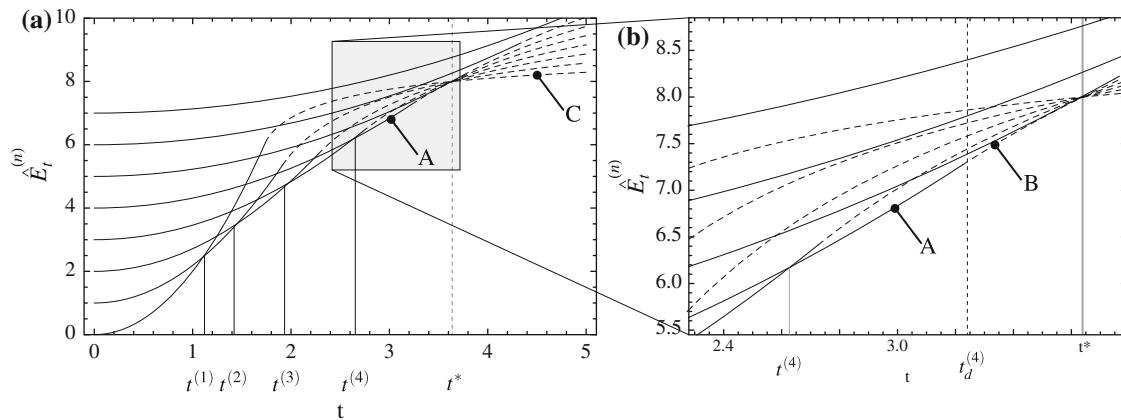


Fig. 7 Energy curves $\hat{E}_t^{(n)}$ with possible debonding and transverse fracture for $\gamma = 2.2, L = 6$. Each curve is for a specific number $n - 1$ of transverse fractures, corresponding to the value at the intersection with the axis $t = 0$. The *solid continuous lines* indicate the energy is obtained for a state without debonding, the *dashed line* for a state with debonding

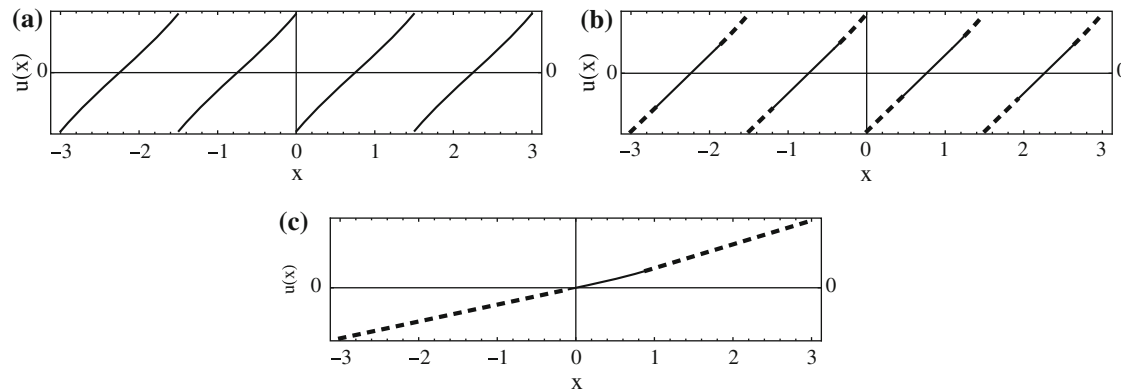


Fig. 8 The optimal displacement fields for the states A, B, C of Fig. 7. Debonded regions are indicated with a *dashed line*

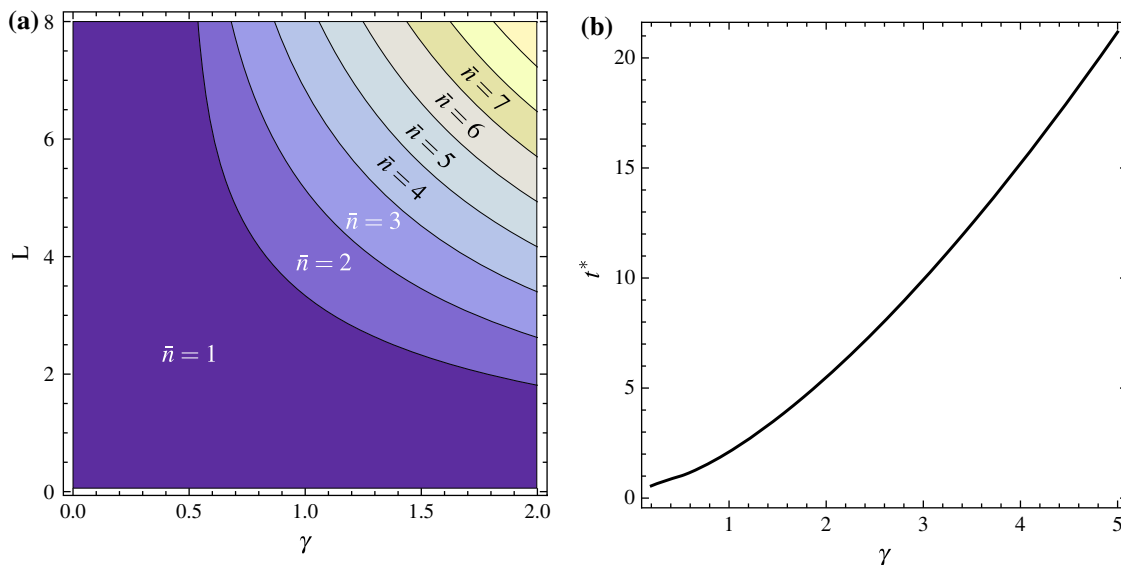


Fig. 9 Key properties of the solution of the static problem of a film of dimensionless length L and relative debonding toughness γ (see Proposition 4). **a** Plot of \bar{n} as a function of L and γ , \bar{n} being the minimum number of pieces into which the film is split by transverse fractures when debonding appear. **b** Plot of t^* as a function of the relative debonding toughness γ , t^* being the critical load beyond which the optimal solution is that of a debonded film without transverse fractures (t^* is independent of the dimensionless length L of the film)

5 The time-continuous quasi-static evolution

We illustrate now some of examples of time-continuous evolutions $t \rightarrow (u_t \in \mathcal{C}(\Gamma_t), \Gamma_t \in \mathcal{A}, \Delta_t \in \mathcal{A})$ satisfying the items (IR), (GST) and (EB) under a monotonically increasing load (MIL) of the type of Eq. (11). We will take as initial state at load $t = 0$ the uncracked solution ($u = 0, \Gamma = \emptyset, \Delta = \emptyset$). The time-continuous evolutions are constructed on the basis of the results of the static analysis of the previous section, by using the fact that all the static solutions *a fortiori* verify the (GST) condition (see the remark at the beginning of Sect. 4). The (EB) condition is met by imposing the continuity of the total energy with respect to the load t , a requirement which is verified also by the static solutions reported in Figs. 4, 5, and 7. A major novelty will be the introduction of the irreversibility condition (IR) of Eq. 8.

5.1 Perfectly bonded film subject to transverse cracks only

In the case without debonding ($\Delta = \emptyset$), the static analysis of Sect. 4.2 (Proposition 1) concludes that the state with $n - 1$ cracks partitioning the domain in n regions of length L/n is optimal in the sense of the global stability condition (GST) for the load t in the interval $(t^{(n-1)}, t^{(n)})$, given by Eq. (21). The critical loads of Eq. (21) are a strictly increasing sequence with respect to n , thus for an initially sound film, the first critical load is $t^{(2)}$ and failure consists in one add-crack in the middle of the film. After the first crack, the irreversibility condition (IR) imposes a restriction on the admissible crack sets. Since the arrangement of the cracks is that of an equi-distributed array, the irreversibility condition turns out to restrict the number $n - 1$ of admissible cracks. The requirement for the admissible crack set to contain all the previous ones implies that, after the first crack, the next possible crack set is the one with two added cracks in the middle of each segment, and so on. In summary, the admissible crack sets must be of the form of $n_j - 1$ equally spaced cracks splitting the film in n_j pieces of length L/n_j , with $n_j := 2^j, j \in \{0, 1, 2, \dots\}$, i.e. the number of pieces has to be a power of two. Hence, the time-continuous quasi-static evolution of the crack set of an initially sound film is found specializing the results of Proposition 1 to this case. In particular, the solution of the evolution problem is with $n_j - 1$ equally spaced cracks for loadings in the interval $t^{(n_{j-1})} < t < t^{(n_j)}$ with $t^{(n_j)} = t_f(L/n_j)$, $t^{(0)} = 0$, where

$$t_f(L) = \frac{1}{\sqrt{2 \tanh \frac{L}{4} - \tanh \frac{L}{2}}}, \quad (39)$$

is the critical load for which a sound film of length L is split in two equal parts by a transverse crack in the middle. The total energy of the solution obtained in this way and the number or segment n versus the load t are plotted in Fig. 10a, b, respectively. These figures emphasize how the irreversibility condition introduces a further selection among the admissible energy minimizers.

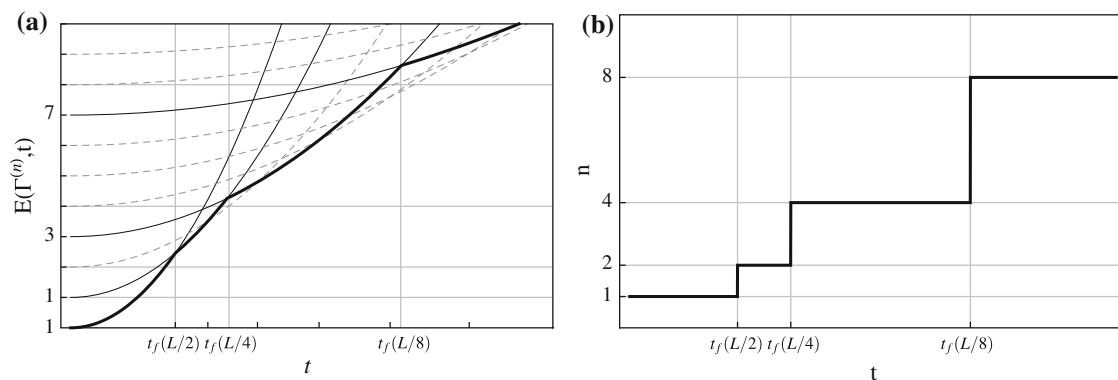


Fig. 10 Quasi-static evolution without debonding: **a** energy curves $E(\Gamma^{(n)}, t)$ versus t for different n , where the *thick solid line* denotes the global minimum corresponding to the solution of the evolution problem; **b** number of parts n_j of length L/n_j versus t formed by the $n_j - 1$ equally spaced cracks, with $n_j = 2^j$

5.2 Perfectly elastic film subject to debonding only

After the static solution of the debonding problem without cracks, its quasi-static counterpart is quite trivial. The irreversibility condition is a twofold requirement: on one hand, the size of the debonded domain must be non-decreasing; on the other hand, a stronger *pointwise* irreversibility must be ensured. This means that if at point x the film is debonded at a time t , it has to be so for all $\tau > t$. The first requirement is automatically satisfied by the static solution given in Proposition 2. Indeed, the bonded length B_t given in Eq. (32) is strictly decreasing with t . The second condition is fulfilled provided that the lengths of the debonded intervals $D_1(t)$ and $D_2(t)$, in the definition of the displacement field of Eq. (28), are arbitrary *non-decreasing* functions of t . Hence, the result synthesized in Proposition 2 holds for the quasi-static evolution for the debonding problem replacing “ D_1 and D_2 are arbitrary” with “ $D_1(t)$ and $D_2(t)$ are arbitrary non-decreasing functions of t ”. In the case of a quasi-static evolution, these results may be interpreted saying that a bar of dimensionless length L and relative cracking toughness γ does not debond for $t < t_b(L, \gamma)$. At $t = t_b(L, \gamma)$, it starts debonding, and the length of the (unique) bonded interval is $L_b(t, \gamma)$.

5.3 Film subject to coupled transverse cracks and debonding

The analysis of the static problem in the coupled case concludes with the Proposition of 3 and 4, which are the starting point to construct solutions of the corresponding quasi-static problem. Irreversibility imposes that the number of transverse cracks are in the form $n_j = 2^j - 1$, with $j \in \mathbb{N}$ non-decreasing with t , and that the debonded domain is non-decreasing with t . For an imposed number $n - 1$ of transverse cracks, the static solution given in Proposition 2 may be directly transposed to the quasi-static setting. Debonding starts appearing at the same time in each segment, at the critical load $t_b(L/n, \gamma)$ given by Eq. (34). The energy of the solution is given by $\hat{E}_t^{(n)}$ of Eq. (38). The length of the bonded part in each piece is L/n for $t < t_b(L/n, \gamma)$ and $L_b(t, \gamma)/n$ for $t > t_b(L/n, \gamma)$, with $L_b(t, \gamma)$ given by Eq. (33). This solution respects the irreversibility because $L_b(t, \gamma)$ is non-increasing with t . Of course, the lengths of the debonded domains in each piece, $D_{1,i}$ and $D_{2,i}$, must be non-decreasing functions of t .

The determination of the evolution of the optimal number of transverse cracks is not an easy problem, in the general case. We illustrate here a typical quasi-static evolution for specific values of the film parameters L and γ when starting from a sound film at $t = 0$. We trace for each admissible value of n in the form $n_j = 2^j$ the corresponding total energy as a function of the loading t , according to Eq. (38) (gray lines in Fig. 11a). The evolution of the film satisfying the (GST) and (IR) conditions is the one corresponding to the lowest value of the energy and marked with a thick black stroke in Fig. 11a. This evolution satisfies also the energy

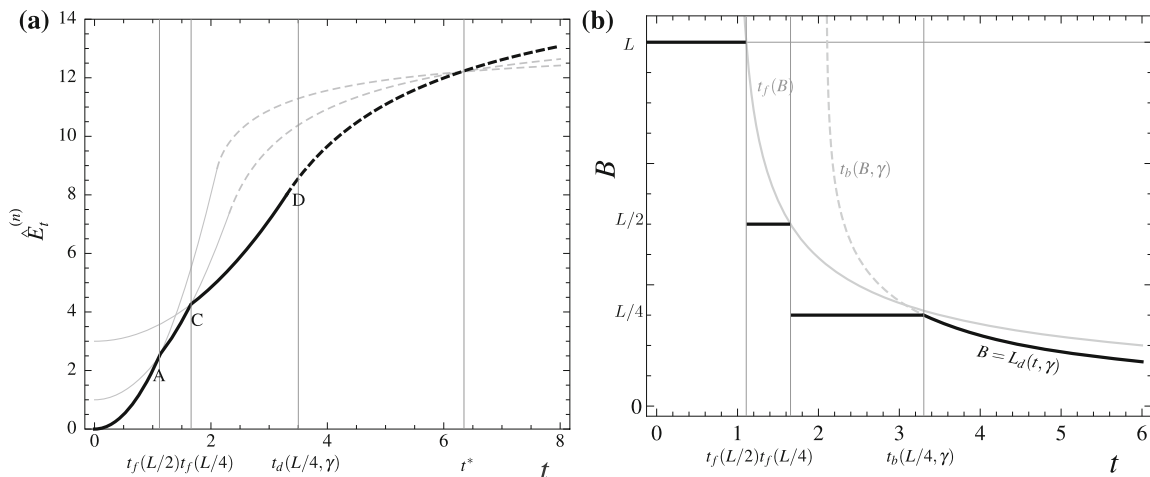


Fig. 11 Quasi-static evolution of an initially sound thin film of length $L = 6$, with $\gamma = 2.2$. **a** In gray, total energies calculated according to Eq. (38) as a function of the load t for different number of film pieces, the bonded states being marked by the dashed stroke. In black, the energy of the quasi-static evolution respecting (GST), (IR) and (EB). **b** In black, the length B of the bonded interval in each film piece as a function of the load t . The *continuous and dashed gray lines* are the critical loads for transverse cracking and debonding of a sound film of length B given by $t_f(B)$ and $t_b(B, \gamma)$, respectively

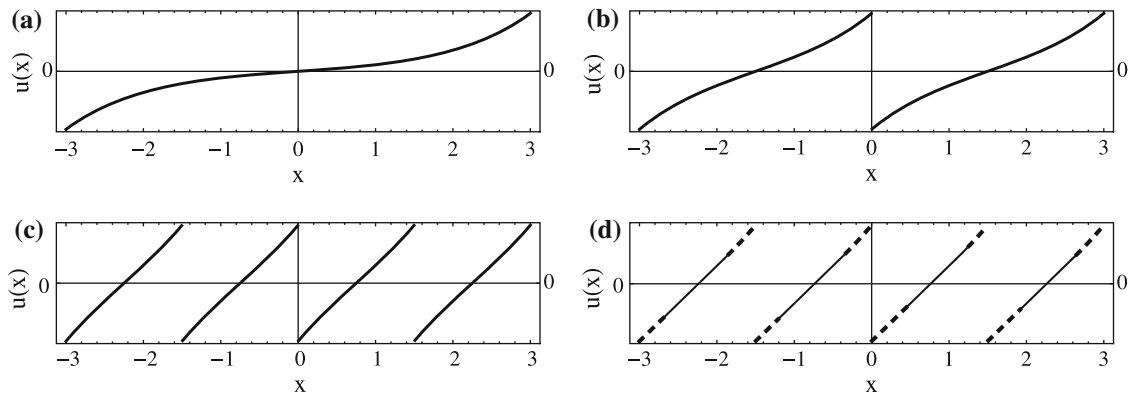


Fig. 12 Snapshots of the displacement field for states O, A, C, D of Fig. 11a. The debonded region is indicated with a *thicker dashed line*

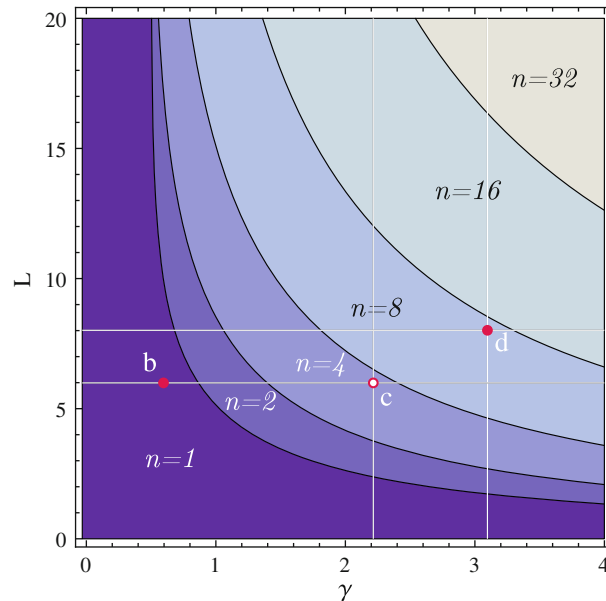


Fig. 13 Phase diagram for the coupled transverse cracking and debonding problem. For a quasi-static evolution, to each couple of parameters (L, γ) the phase diagram associates the (maximum) number of parts n into which the film is split before debonding takes place. We point out with a *white dot* the couple of parameters of the evolution illustrated in Sect. 5.3, with a *red dot* the couples of parameters referring to the numeric experiments detailed in Sect. 6 (color figure online)

balance (EB) because of the continuity of the energy and is therefore a well-defined solution of the quasi-static evolution problem. The corresponding displacement fields of the film are illustrated in Fig. 12. Figure 11b reports the evolution of bonded length in each segment (thick black stroke). At $t = 0$, it is equal to the total length of the sound bar. At the point A, which corresponds to the intersection with the curve $t_f(B)$ given by Eq. (39) and marked with a thin solid gray stroke in Fig. 11b, the film breaks in $n = 2$ parts without debonding. Then, the bonded length in each segment is $B = L/2$, till the next intersection with the line $t_f(B)$ at point C, where each part further splits in two totally bonded segments of length $B = L/4$. At point D, the load reaches the critical debonding time $t_b(B, \gamma)$ of Eq. (34). Here, the film split into $n = 4$ pieces starts debonding. No further transverse crack appears for higher loading.

More in general, there may be a cascade of j transverse cracks followed by debonding. An interesting property of the solution is the number n_j , which is the maximum number of pieces (of equal length) in which the film splits before delamination. As done in the static problem, this number is obtained by looking for the smallest integer value of j for which $t_b(L/n_j, \gamma) < t_f(L/n_j)$. Figure 13 reports a phase diagram giving the n_j obtained in this way as a function of the relevant parameters L and γ .

6 Numerical experiments

6.1 Implementation

The numerical approach we use is derived from the one presented in depth in [12, 13]. It is based on a variational approximation of the total energy $\tilde{\mathcal{E}}_t$ in (6) by elliptic functionals, originally proposed in [19, 20] for the approximation of the Mumford–Shah problem in image processing. In the setting of [12, 13], one can introduce a function α taking its values in $[0, 1]$ and representing in some sense the crack set, a regularization parameter η homogeneous to a length, and a regularized energy depending on the parameter η . It is then possible to show that this energy converge in the sense of Γ -convergence to the fracture total energy, from which one derives convergence of global minimizers (see [24] for instance, for more details on the construction of the regularized energy). This analysis can then be carried out for the time evolution as shown in [25].

Here, we proceed by induction. We modify the regularized functional originally used in [12] to account for the inelastic strain and the debonding terms. For any u , α , and any function δ with values in $\{0, 1\}$ representing the debonded area, we consider a regularized energy in the form

$$\begin{aligned} \tilde{\mathcal{E}}_{t,\eta}(u, \alpha, \delta) := & \int_{\mathcal{A}} \frac{1}{2} (1 - \alpha(x))^2 (u'(x) - t)^2 \\ & + \frac{1}{2} u(x)^2 (1 - \delta(x)) + \gamma \delta(x) + \frac{3}{8} \left(\frac{\alpha(x)}{\eta} + \eta \alpha'(x)^2 \right) dx. \end{aligned} \quad (40)$$

The surface energy term $\frac{3}{8} \int_{\mathcal{A}} \frac{\alpha}{\eta} + \eta \alpha'^2 dx$ differs from the one used in [12] while still falling with the more general scope of [24]. A comparison of the properties of both approximations can be found in [26].

We approach the time-continuous quasi-static evolution (CEL) by a time-discretized regularized evolution law by considering a discrete set of loads t_i , and iteratively seeking global minimizers $(u_i, \alpha_i, \delta_i)$ of $\tilde{\mathcal{E}}_{t_i,\eta}$ under the crack growth condition $\alpha_i \geq \alpha_{i-1}$ and $\delta_i \geq \delta_{i-1}$. This time-discrete minimization problem is in turn discretized in space by means of linear finite elements, following the lines of past work cited above. We made no attempt at proving the convergence of the regularized model or its discretization to the continuous evolution law, a technical task beyond the scope of this article and under current investigation. Still, we expect that as $\eta \rightarrow 0$, the solution of the time-discrete regularized model converge to that of the continuous time evolution and, in particular, that the function α converges to 1 “along the cracks” and to 0 “away from the cracks”, that the bulk term $\frac{1}{2} \int_{\mathcal{A}} (1 - \alpha)^2 (u' - t)^2 dx$ converge to $\frac{1}{2} \int_{\mathcal{A} \setminus \Gamma} (u' - t)^2 dx$, and that $\frac{3}{8} \int_{\mathcal{A}} \left(\frac{\alpha}{\eta} + \eta \alpha'^2 \right) dx$ converges to the number of cracks in the domain.

The numerical minimization of the regularized energy is challenging as it is non-convex and stiff. For each loading parameter t_i , we take advantage of the fact that $\tilde{\mathcal{E}}_{t_i,\eta}$ is separately convex in the variables u , α and δ and alternate minimization with respect to u , δ , and α until convergence. Minimization with respect to the displacement field u is a straightforward unconstrained optimization problem implemented using a pre-conditioned conjugated gradient algorithm. Following Lemma 1, we know that for any t_i , the optimal δ_i is a characteristic function (i.e., no relaxation phenomenon takes place), and moreover that for a given u and α , the optimal function $\delta(x)$ is such that $\delta(x) = 1$ if $u(x) \geq \sqrt{2\gamma}$ and 0 otherwise. Finally, minimization with respect to α is a box constrained problem.

It is well known that such an algorithm applied to a non-convex energy may not converge to a *global* minimizer, but only to a critical point. In the case of the uncoupled problems (transverse fracture or debonding only), this can be mitigated by implementing a *backtracking algorithm*, relying on a necessary condition for optimality with respect to the time evolution, and a construction of an evolution that satisfies it (see [27]). In the current situation, when the competition takes place between three terms in the energy, a similar optimality condition can be written, but the construction of an evolution satisfying it is not as straightforward, and the results presented in the sequel do not use a backtracking algorithm. Note, however, that the results of Lemmas 1 and 2 about the general properties of solutions with debonding only require that first-order optimality conditions be satisfied and therefore hold for local minimizers and critical points of the total energy. Finally, note that there is always a debate surrounding global minimality as the proper framework. In short, global minimality may sometimes lead to unphysical evolutions, but local minimality typically forbids transverse crack initiation without singularities, the essence of the one-dimensional model. We do not take part in this debate, but notice that in most cases, in our experiments, transitions between energy-minimizing states are driven by the loss of their stability, which in turn is sensitive to the parameter η , (see [26]).

We conclude the description of the numerical approach by two remarks. First, as we focus here on the simple one-dimensional situation, our numerical experiments do not illustrate one of the strengths of our approach, its ability to handle complicated crack geometries and topologies. In the one-dimensional setting, there are methods based on dynamic programming that are guaranteed to converge to global minimizers of the total energy. Of course, this is at the cost of versatility as these do not generalize easily to the multi-dimensional case. In contrast, our approach is suited to the numerical simulation of real two-dimensional problems, in situations where complicated crack and debonding geometries are expected, a strength that is not fully exploited in the present work. Secondly, the regularized energy (40) is similar to a non-local damage model where α is a damage parameter and η an internal length. In the current study, however, we see this as a mere coincidence. We only think of η as a numerical regularization parameter and of $\tilde{\mathcal{E}}_{t,\eta}(u, \alpha, \Delta)$ as an approximation of (6), taking place as $\eta \rightarrow 0$.

We propose to use this numerical approach to illustrate the various results presented in the previous sections, starting with quasi-static transverse fracture and debonding separately, then coupling both fracture modes. In addition to the scaling (7), we modify the toughness γ in order to account for the interaction between the mesh discretization and regularization parameters as in [13].

For each experiment we present, we use the following convention: in the energy plots, the total energy is plotted in bold solid line, the energy associated with the transverse cracks in dashed lines, that associated with the debonding in dot-dashed lines, and the elastic energy in thin solid lines. When applicable, the total energy of the closed-form solution is also plotted in light dashed lines, and the relevant critical loads indicated by vertical dashed lines. When we plot the displacement and the α field representing the cracks, the displacement is depicted in thick solid lines and α as a thin line. When we plot the displacement and the debonding characteristic function δ , the displacement is depicted in thick solid lines and δ as a thin line. The displacements are normalized so that they take values in $(-1, 1)$. The debonded area corresponding to $\delta(x) = 1$ is highlighted in light gray.

6.2 Numerical simulation of a perfectly bonded film subject to transverse cracks only

We focus first on the case of a perfectly bonded film studied in Sect. 4.2 where only transverse cracks are allowed. This is achieved by forcing $\delta \equiv 0$ in our numerical scheme. We consider a domain of length $L = 6$, decomposed into 600 linear finite elements ($h = 10^{-2}$). The load history $[0, T_{\max}]$ is discretized with 600 time steps of equal length. The regularization parameter η is set to 5.5×10^{-2} .

Figure 14 presents the outcome this experiment. The snapshot of the displacement and damage fields in Fig. 14b is taken at the last time step of the load path. The equi-distributed fracture pattern is correctly captured, indeed the peaks of the damage field representing the location of cracks occur at $x = -1.5, 0, 1.5$ in Fig. 14b. Moreover, the damage field has continuous derivative except at its peaks and decays rapidly to 0. In the energy plot, the first branch of parabola corresponds to the elastic loading of the sound film. At $t = 1.78$, the first transverse fracture appears at the center of the film, which leads to a sudden increase of the surface energy at the expense of elastic energy. As the loading increases, the system follows the second branch of parabola, i.e. the elastic loading of the *two* pieces into which the original film is split. The second critical load $t = 2.60$ corresponds the opening of two cracks along the center of each film piece. The final snapshot of the fracture profile is shown in Fig. 14b. As hinted above, the mechanisms leading to bifurcation between branches of energy is the loss of stability and is η -dependent leading us to overestimate the value of the critical loads. In this situation, a backtracking algorithm would have allowed the reconstruction of the proper energy profile. We also note that in this situation, the displacement field is not perfectly antisymmetric with respect to the center of each of film pieces as expected. This is due to the fact that whereas the free boundary condition is exactly satisfied at the end point of the domain, it is only *asymptotically* satisfied as $\eta \rightarrow 0$ along the crack. Indeed, in Fig. 14b, one can see that the displacement magnitude is slightly larger at the boundary of the domain than at the cracks edges. As we will see below, this will have an effect on the debonding evolution in coupled simulations.

6.3 Numerical simulation of a perfectly elastic film subject to debonding only

We continue our numerical investigations by focussing on the situation considered in Sect. 5.2 where only debonding is allowed. Again, this is easily achieved by skipping the minimization with respect to α and forcing

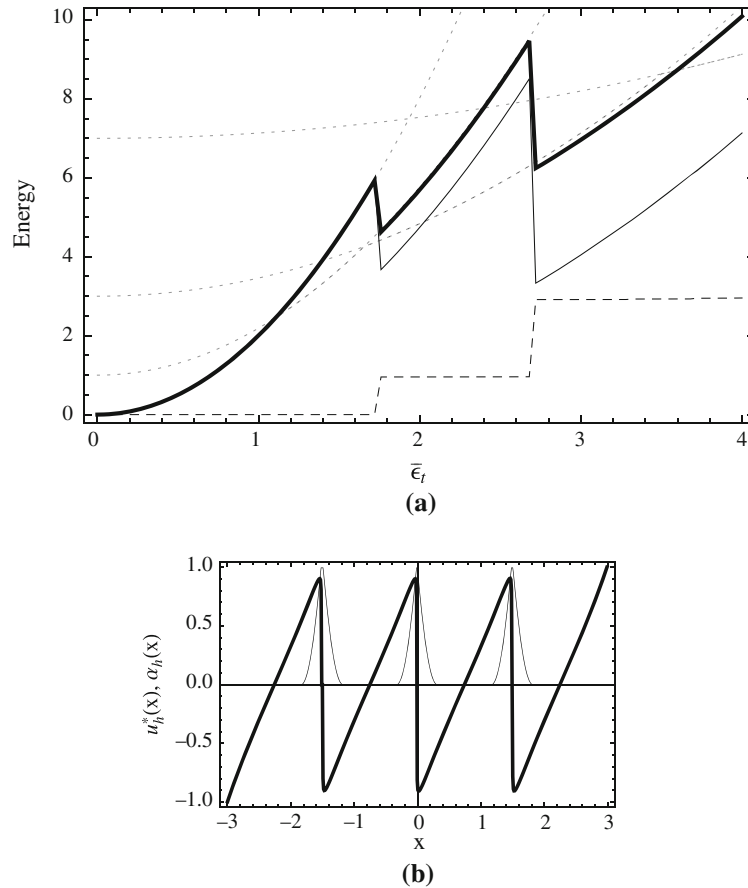


Fig. 14 Uncoupled numerical experiment allowing only transverse cracks. **a** Evolution of the system total (*thick line*), elastic (*thin line*) and surface energies (*dashed*). The total energy of the crack states studied in Sect. 4.2 is shown in *light dashed curves*, **b** at the end of the loading phase three transverse cracks are obtained, represented by the localization the field α on a narrow zone. In our regularized formulation, discontinuities of the displacement are replaced with zones with very high gradient

$\alpha \equiv 0$ throughout the domain. The discretization parameters are identical to that above, and the parameter γ arbitrarily set to 0.5. Figure 15 presents the outcome of our numerical experiments. The fields u and δ at the last time step are shown in Fig. 15b. The area where $\delta(x) = 1$ is highlighted in gray. As predicted in Proposition 2, the debonded area consists in two segments originating from each end of the domain. Although the analytic solution is not unique, our numerical solution seems to favor a symmetric solution. On the debonded domain, the displacement is linear and the deformation gradient is identically equal to the imposed inelastic strain.

The energy plot is shown in Fig. 15a. The critical load of 1.01 at which debonding takes place in the closed form solution in (33) is denoted by a vertical thin line. The critical load we obtained in the numerical experiment is 1.04, a relative error of 3%. The comparison of the total size of the debonded domain yields $B = 5.66$ using Eq. (32), and $B_h = 5.67$ for the numerical experiment, a relative error of 0.1%. The surface energy related to debonding increases as $L - L_b(t)$. The total energy grows asymptotically to reach a value of γL of a fully debonded film.

The obtained evolution matches perfectly that obtained in Sect. 5.2. This is not really a surprise as the solution is given by the first order optimality conditions (31) which are implemented in the minimization algorithm.

6.4 Numerical simulation of a film subject to coupled transverse cracks and debonding

We finally present two numerical experiments implementing the fully coupled model. In the first one, the geometry and spacial discretization parameters are unchanged. The load increment is set to 10^{-2} and the parameter γ to 2.2, matching the example from Fig. 11 in Sect. 5.3.

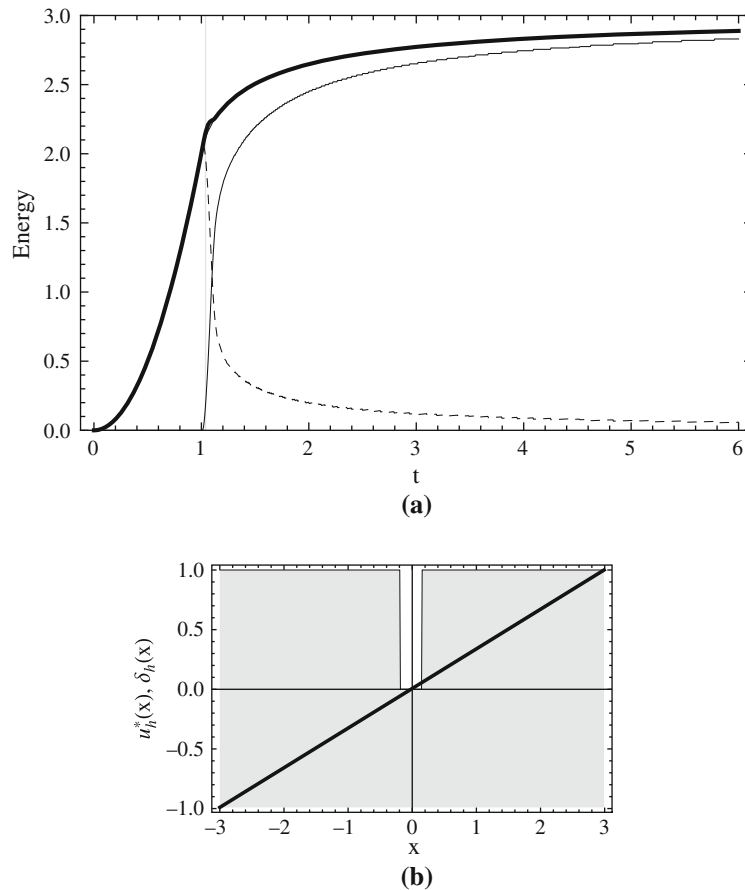


Fig. 15 Uncoupled numerical experiment allowing only debonding. **a** Energy plot for the uncoupled debonding experiment. After an elastic loading phase, the film undergoes debonding. The total energy has a horizontal asymptote that corresponds to the energy of the totally debonded film, **b** plot of the displacement field and the debonded domain (shown shaded in light gray) shaded field. As expected, debonding initiates at the edge of the domain and propagates toward its center. The displacement is linear on the debonded domain

In the first numerical experiment, we observe the nucleation of a transverse crack at the center for a load $t = 1.59$, instead of the predicted $t = 1.04$. Again, this is due to the fact that in the numerics, the bifurcation from the uncracked configuration to the cracked one is governed by loss stability of the elastic solution, and not global minimality. For similar reasons, we do not observe the initiation of cracks on each of the ligaments as predicted in Sect. 5.3. However, as expected, debonding expanding from the crack tip occurs at a load of $t = 1.98$ (an error of 0.2% compared to the theoretical value), and the evolution of the total debonded length follows the one predicted in Fig. 11. In particular, the size of the debonded domain at the end of the loading phase is 7.34, matching the predicted value within 3%. The value of the first critical load could be improved using a backtracking argument. However, since we do not observe nucleation of secondary cracks, but instead directly detect debonding, a simple backtracking argument will not suffice to identify the missed bifurcation. Plots of the energy curves, displacement and debonding fields are shown in Fig. 16.

In order to qualitatively recover the richness of the evolution described in Sect. 5.3, we consider a second numerical simulation of a domain of length 8, discretized into elements of size 1.6×10^{-2} (Fig. 17).

In this situation, we first obtain a centered transverse crack a $t = 1.56$, followed by the simultaneous initiation of two cracks, centered around each piece of film at a critical load $t = 2.04$. Only at this point is debonding of the film taking place. As hinted in Sect. 6.2, the displacement field is not perfectly antisymmetric in the first and last ligament, causing debonding to initiate there slightly earlier than at the film's cracks. This can be seen in Fig. 17c where the debonded region is not symmetric in the outmost film pieces $(-4, -2)$ and $(2, 4)$. The energy evolution we recover matches the prediction with a bonded area decreasing as $L_b(t)$ and a debonding energy proportional to $L - L_b(t, \gamma)$ as in Eq. 33. The numerical critical debonding load is 3.12, and it underestimates the critical load for debonding $t_b(L/4) = 3.24$ computed with Eq. (34).

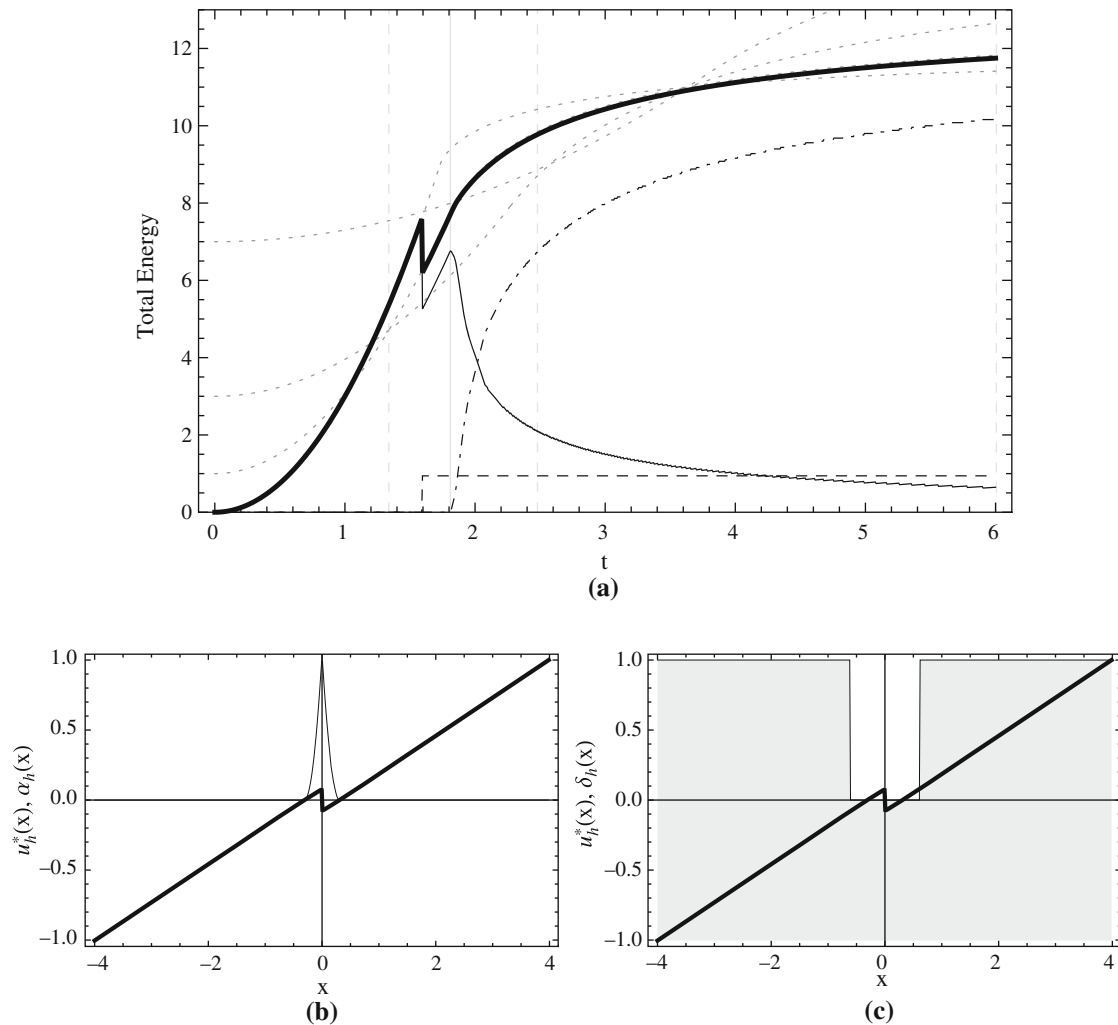


Fig. 16 Coupled experiment #1: transverse fracture and debonding. One transverse fracture and then delamination. **a** Energy plot of the evolution, after a sound loading phase, the system jumps to the fractured state with one crack. The energy is discontinuous at the transition load. Then debonding starts respecting energy continuity, **b** plot of the displacement and damage field. The crack appears in the middle of the film, **c** plot of the displacement and the debonded domain. It is symmetric with respect to the center of the film

7 Conclusions

We applied the variational approach to fracture mechanics to study fracture and debonding of a thin film bonded on a stiff substrate. Our analysis is based on a 1D reduced model where transverse cracks and debonding are introduced through a surface energy of the Griffith type, the bulk energy being assumed to be linear elastic up to failure. The presence of the substrate is accounted for by an equivalent elastic foundation. We made no attempt here to present a rigorous justification of the model starting from the 3D description, but instead we performed a detailed analysis of its solutions and their qualitative properties.

In the reduced model, transverse and debonding cracks appear with a different geometric nature. Whereas the first are of geometrical co-dimension 1 (points in 1D and surfaces in 2D), the second are of co-dimension 0 (segments in 1D and surfaces in 2D). Only transverse cracks introduce discontinuities in the displacement fields. This difference entails a distinct mathematical and numerical treatment and solutions with disparate qualitative properties. This point has been emphasized by presenting separately the solutions of the transverse fracture and debonding problems, before tackling the more complex coupled case. For debonding without transverse cracks, the main result is that the bonded part of the domain is a single connected segment, which

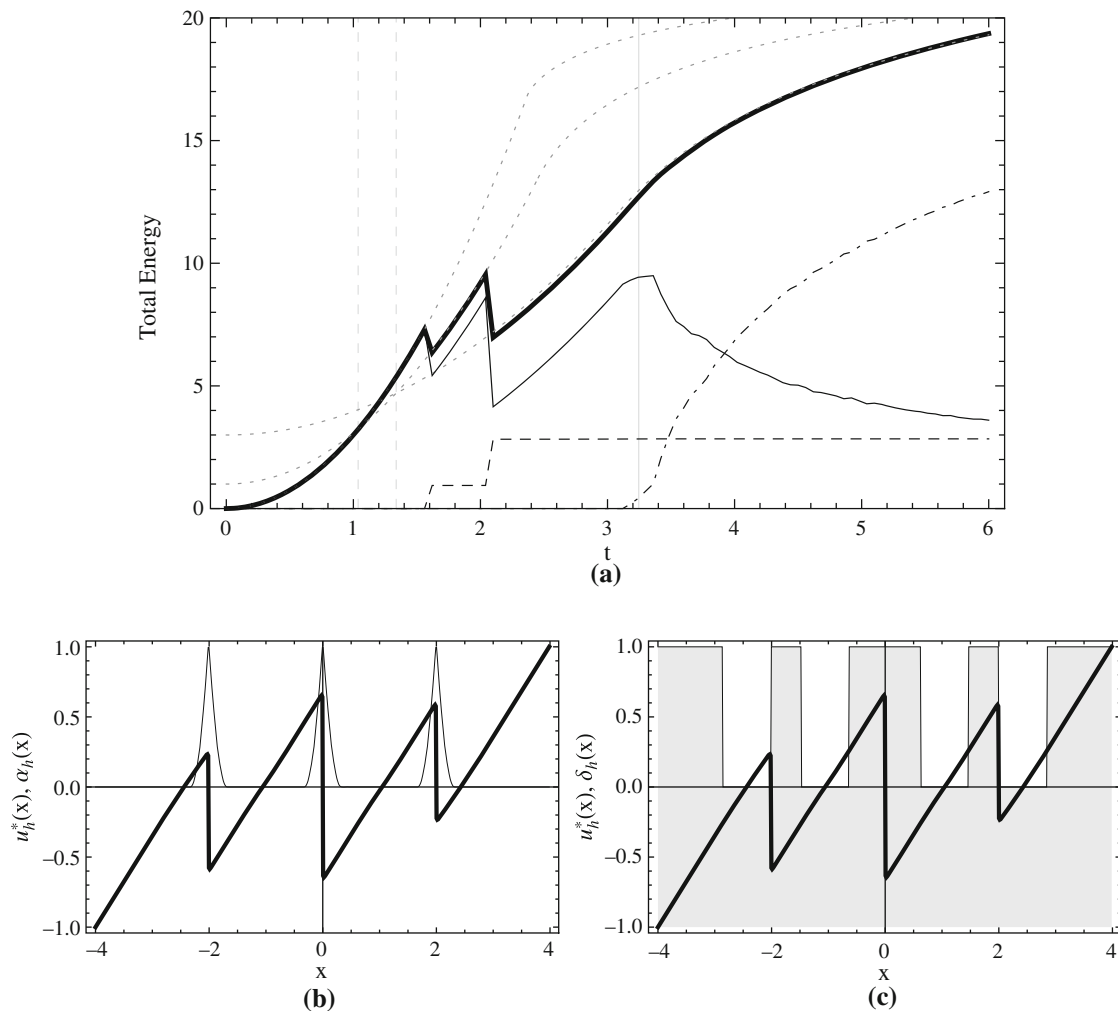


Fig. 17 Coupled experiment #2: transverse fracture and debonding. Three transverse fractures and debonding. **a** Energy plot shows an evolution consisting in three subsequent transverse fractures and debonding. Boundary layer effects appear during the very first phase of debonding, as the linear growth of the debonding energy in the very first debonding phase indicates, **b** plot of the displacement and damage fields, the film exhibits three transverse cracks at the end of the loading phase, **c** plot of the displacement and debonded domain (shaded in *light gray*). The latter is not symmetric for each part of the *bar* since the total energy is insensitive to the arrangement of the debonded domain

is uniquely determined as a function of the loading. Equivalently, debonding may appear only at the ends of the domain. Moreover, this is a property true of all local minima of the energy.

The modeling of transverse cracks requires us to formulate problem in terms of global minimization, as customary in the variational approach to fracture mechanics with a Griffith-type surface energy. We showed that transverse cracks are equally spaced and lead to periodic solutions. This behavior was only postulated in previous studies. The coupling of transverse fracture and debonding produces an interesting and rich behavior even in the 1D setting. Through analytical results and phase diagrams, we unveiled the dependence of the key qualitative properties of the solutions on the two non-dimensional parameters of the model. In the numerical part, we proposed a finite elements implementation of a regularized model. Our numerical approach is used to illustrate key properties of the model identified in the analysis section. A natural extension of this work is to tackle the 2D case, which is known to lead to intriguing complex crack and debonding patterns, like fracture networks, parallel crack arrays with stop-and-go phenomena, or spirals. The extension of the numerical model to 2D is straightforward. It is under active development, and the analytical results presented here will be used for its verification. The rigorous derivation of the thin-film model with fracture and debonding, starting from a 3D variational model with Griffith surface energy is pending. Preliminary Γ -convergence results are available and will be reported in a forthcoming paper. Our final aim is to compare the analytical and numerical

findings to experimental evidences. Collaborations with experimentalists in the thin-film domain are currently in progress.

Acknowledgments This joint work was financed by the French National Research Council CNRS in the framework of a joint international research program PICS. B. Bourdin's work was supported in part by the National Science Foundation under the grant DMS-0909267. J.-J. Marigo and C. Maurini gratefully acknowledge the funding of the ANR program T-Shock OTP J11R087. C. Maurini and A. A. León Baldelli work was partially supported by University Pierre et Marie Curie in the framework of an EMERGENCES-UPMC grant.

Appendix

Proof (of Lemma 1) We consider a sound bar $\Gamma = \emptyset$ and let u be a local minimizer of $\tilde{\mathcal{E}}_t(u, \emptyset)$. Let us first prove that there exists $x \in [-L/2, L/2]$ such that $|u(x)| < u_c$, by contradiction. Let us consider the following family of admissible displacement fields $v_h = u + hv$ with $h > 0$ and $v \in \mathcal{C}(\emptyset)$. Since v_h converges to u as $h \rightarrow 0$, we must have for h sufficiently small

$$0 \geq \tilde{\mathcal{E}}_t(u, \emptyset) - \tilde{\mathcal{E}}_t(v_h, \emptyset) = \int_{-L/2}^{L/2} (2h(u' - t)v' + h^2v'^2 + f(|u(x)|) - f(|v_h(x)|)) dx. \quad (41)$$

Since $f(|u(x)|) = \gamma \geq f(|v_h(x)|)$, one gets $0 \geq \int_{-L/2}^{L/2} (2h(u' - t)v' + h^2v'^2) dx$. Dividing by h and passing to the limit as $h \rightarrow 0$, one obtains $\int_{-L/2}^{L/2} (u' - t)v' dx = 0$, equality which must hold for every $v \in \mathcal{C}(\emptyset)$. It is possible only if $u' = t$. Inserting this relation into (41) leads to a contradiction. Therefore there exists $x \in [-L/2, L/2]$ such that $|u(x)| < u_c$.

Then, let us prove that u has (at least) a zero in $[-L/2, L/2]$, still by contradiction. Suppose that u has the same sign on $[-L/2, L/2]$, say $\varepsilon = \pm 1$. For $h \in (0, \min |u|)$, let us consider the following family of admissible displacement fields v_h :

$$v_h(x) = u(x) - \varepsilon h.$$

Since v_h converges to u as $h \rightarrow 0$, we must have for h sufficiently small

$$0 \geq \tilde{\mathcal{E}}_t(u, \emptyset) - \tilde{\mathcal{E}}_t(v_h, \emptyset) = \int_{[0, L]} f(|u(x)|) - f(|v_h(x)|)$$

But since $|v_h(x)| < |u(x)|$ and since f is strictly increasing in the interval $[0, u_c]$, the above inequality can be satisfied only if $|u(x)| \geq u_c$ for all x . But we have proved before that it is impossible. Therefore u has at least a zero.

We are now in a position to prove that u is monotonic, by contradiction. If $u(x)$ is not monotonic, then it has a positive local maximum or a negative local minimum in $(-L/2, L/2)$ and we can find $U \in \mathbb{R}$ such that there exist $-L/2 \leq a < b \leq L/2$ verifying:

$$u(a) = u(b) = U \quad \text{and} \quad |u(x)| > |U|, \quad \forall x \in (a, b)$$

For $h \in (0, 1)$, let us consider the following family of admissible displacement fields v_h :

$$v_h := \begin{cases} u(x), & \text{if } x \notin (a, b) \\ (1 - h)u(x) + hU & \text{if } x \in [a, b] \end{cases}$$

Since v_h converges to u as $h \rightarrow 0$, we must have for h sufficiently small

$$\begin{aligned}
0 &\geq \tilde{\mathcal{E}}_t(u, \emptyset) - \tilde{\mathcal{E}}_t(v_h, \emptyset) \\
&= \int_{[a,b]} (u'(x) - t)^2 + f(|u(x)|) \, dx - \int_{[a,b]} (u'(x)(1-h) - t)^2 - f(|v_h(x)|) \, dx \\
&= \int_{[a,b]} u'^2(x)(1 - (1-h)^2) \, dx - 2h \int_{[a,b]} tu'(x) \, dx + \int_{[a,b]} f(|u(x)|) - f(|v_h(x)|) \, dx \\
&= \int_{[a,b]} u'^2(x)(1 - (1-h)^2) \, dx + \int_{[a,b]} f(|u(x)|) - f(|v_h(x)|) \, dx
\end{aligned}$$

Since both the integrands are non-negative, for the inequation to be satisfied both the integrands must vanish. This leads to $u'(x) = 0$ in (a, b) and since $u(x) = U$ for $x = a, b$ and u must be continuous, one should have $u(x) = U$ in (a, b) which contradicts $|u(x)| > |U|$ in (a, b) . Then $u(x)$ is monotonic. \square

Proof (of Lemma 2) Let $v \in C_0^\infty([-L/2, L/2])$ and $h \in \mathbb{R}$. When $|h|$ is sufficiently small, then $\varphi_h(x) := x + hv(x)$ is a C^∞ -diffeomorphism on $[-L/2, L/2]$. Let $u \in W^{1,2}[-L/2, L/2]$, and define $u_h := u \circ \varphi_h^{-1}$. One has $\lim_{h \rightarrow 0} u_h(x) = u(x)$ pointwise. If u is a local minimizer then $I(u) \leq I(u_h)$ for some sufficiently small h . We compute

$$I(u_h) = \int_0^L \left(\left(\frac{u'(y)}{\varphi_h'(y)} - t \right)^2 + f(|u(y)|) \right) \varphi_h'(y) \, dy$$

The last quantity is differentiable with respect to h , attaining its minimum value for $h = 0$, u being a minimizer. We therefore require that the first derivative with respect to h vanishes for $h = 0$

$$0 = \left. \frac{dI(u_h)}{dh} \right|_{h=0} = \int_0^L (-(u'^2(x) - t^2) + f(|u(x)|)) v'(x) \, dx, \quad \forall v \in C_0^\infty([-L/2, L/2])$$

We easily infer the prime integral: $u'(x)^2 - t^2 - f(|u(x)|) = C$, $\forall x \in [-L/2, L/2]$. Let's compute the boundary conditions. Define $x_h = L/2(1-h)$ for $h \in (0, 1)$ and $\forall \vartheta \in \mathbb{R}$ construct a test field v_h as follows

$$v_h(x) := \begin{cases} u(x), & \text{if } x \in [-L/2, x_h] \\ u(x) + \vartheta(x - x_h) & \text{if } x \in [x_h, L/2] \end{cases} \quad (42)$$

Such a test field is admissible and $v_h \rightarrow u$ pointwise for $h \rightarrow 0$. Let u be a minimizer, then we can write the following inequality

$$\begin{aligned}
0 &\leq \tilde{\mathcal{E}}_t(v_h(x), \emptyset) - \tilde{\mathcal{E}}_t(u, \emptyset) \\
&= \int_{[x_h, L]} (u'(x) - t)^2 + f(|u(x)|) \, dx - \int_{[x_h, L]} (u'(x) + \vartheta - t)^2 - f(|v_h(x)|) \, dx \\
&= \int_{[x_h, L]} \vartheta^2 + 2\vartheta u'(x) - 2\vartheta t + (f(|v_h(x)|) - f(|u(x)|)) \, dx
\end{aligned}$$

dividing the last equation by h and passing to the limit for $h \rightarrow 0$, the term in parentheses vanishes grace to the pointwise convergence $v_h \rightarrow u$ and the inequality

$$0 \leq \vartheta^2 + 2\vartheta(u'(L) - t)$$

has to be verified $\forall \vartheta \in \mathbb{R}$. This leads to the desired boundary condition: $u'(L/2) = t$. Symmetrically we can construct test fields to retrieve the boundary condition on $x = 0$ as follows

$$v_h(x) := \begin{cases} u(x) + \vartheta(x - x_h) & \text{if } x \in [-L/2, x_h] \\ u(x), & \text{if } x \in [x_h, L/2] \end{cases} \quad (43)$$

where now $x_h = h$. We have the same pointwise convergence as above and we derive the boundary condition $u'(-L/2) = t$. \square

References

1. Hutchinson, J.W., Suo, Z.: Mixed mode cracking in layered materials. *Adv. Appl. Mech.* **29**, 63–191 (1992)
2. Timm, D.: Prediction of thermal crack spacing. *Int. J. Solids Struct.* **40**(1), 125–142 (2003)
3. Lazarus, V., Pauchard, L.: From craquelures to spiral crack patterns: influence of layer thickness on the crack patterns induced by desiccation. *Soft Matter* **7**(6), 2552 (2011)
4. Hsueh, C.H.: Analyses of multiple film cracking in film/substrate systems. *Ceramics* **84**(12), 2955–2961 (2001)
5. Zhang, T.Y., Zhao, M.H.: Equilibrium depth and spacing of cracks in a tensile residual stressed thin film deposited on a brittle substrate. *Eng. Fract. Mech.* **69**, 589–596 (2002)
6. Bialas, M., Mroz, Z.: Crack patterns in thin layers under temperature loading. Part I: monotonic loading. *Eng. Fract. Mech.* **73**(7), 917–938 (2006)
7. Bialas, M., Mroz, Z.: An energy model of segmentation cracking of thin films. *Mech. Mater.* **39**(9), 845–864 (2007)
8. Hsueh, C.H., Yanaka, M.: Multiple film cracking in film/substrate systems with residual stresses and unidirectional loading. *J. Mater. Sci.* **38**, 1809–1817 (2003)
9. Kim, S.: Fracture mechanics analysis of coating/substrate systems. Part I: analysis of tensile and bending experiments. *Eng. Fract. Mech.* **65**(5), 573–593 (2000)
10. Xia, Z.C., Hutchinson, J.W.: Crack patterns in thin films. *J. Mech. Phys. Solids* **48**, 1107–1131 (2000)
11. Francfort, G.A., Marigo, J.J.: Revisiting brittle fracture as an energy minimization problem. *J. Mech. Phys. Solids* **46**, 1319–1342 (1998)
12. Bourdin, B., Francfort, G., Marigo, J.J.: Numerical experiments in revisited brittle fracture. *J. Mech. Phys. Solids* **48**(4), 797–826 (2000)
13. Bourdin, B., Francfort, G., Marigo, J.J.: The variational approach to fracture. *J. Elast.* **91**(1–3), 1–148 (2008)
14. Del Piero, G., Owen, D.R.: Structured deformations of continua. *Arch. Ration. Mech. Anal.* **124**, 99–155 (1993)
15. Del Piero, G., Truskinovsky, L.: Macro- and micro-cracking in one-dimensional elasticity. *Int. Jo. Solids Struct.* **38**, 1135–1148 (2001)
16. Del Piero, G., Truskinovsky, L.: Elastic bars with cohesive energy. *Continuum Mech. Thermodyn.* **21**(2), 141–171 (2009)
17. Lancioni, G., Royer-Carfagni, G.: The variational approach to fracture mechanics. A practical application to the French Panthéon in Paris. *J. Elast.* **95**, 1–30 (2009)
18. Mielke, A.: Evolution of rate-independent systems. In: *Evolutionary Equations, Handbook of Differential Equations*, vol. II, pp. 461–559. Elsevier/North-Holland, Amsterdam (2005)
19. Ambrosio, L., Tortorelli, V.M.: Approximation of functional depending on jumps by elliptic functional via Γ -convergence. *Commun. Pure Appl. Math.* **43**(8), 999–1036 (1990)
20. Ambrosio, L., Tortorelli, V.: On the approximation of free discontinuity problems. *Bollettino Della Unione Matematica Italiana. Serie VIII. Sezione B* **6**(1), 105–123 (1992)
21. Nguyen, Q.S.: *Stability and Nonlinear Solid Mechanics*. Wiley, London (2000)
22. Nagl, M.M., Saunders, S.R.J., Evans, W.T., Hall, D.J.: The tensile failure of nickel oxide scales at ambient and at growth temperature. *Corros. Sci.* **35**, 965–977 (1993)
23. Marigo, J.J., Truskinovsky, L.: Initiation and propagation of fracture in the models of Griffith and Barenblatt. *Continuum Mech. Thermodyn.* **16**(4), 391–409 (2004)
24. Braides, A.: Approximation of free-discontinuity problems. In: *Lecture Notes in Mathematics*, vol. 1694. Springer (1998)
25. Giacomini, A.: Ambrosio–Tortorelli approximation of quasi-static evolution of brittle fractures. *Calc. Var. Partial Differ. Equ.* **22**(2), 129–172 (2005)
26. Pham, K., Amor, H., Marigo, J.J., Maurini, C.: Gradient damage models and their use to approximate brittle fracture. *Int. J. Damage Mech.* **20**(4, SI), 618–652 (2011)
27. Bourdin, B.: Numerical implementation of the variational formulation of quasi-static brittle fracture. *Interfaces Free Boundaries* **9**, 411–430 (2007)